

Polyoxometalate clusters, nanostructures and materials: From self assembly to designer materials and devices

De-Liang Long, Eric Burkholder and Leroy Cronin*

Received 8th August 2006

First published as an Advance Article on the web 30th October 2006

DOI: 10.1039/b502666k


Polyoxometalates represent a diverse range of molecular clusters with an almost unmatched range of physical properties and the ability to form structures that can bridge several length scales. The new building block principles that have been discovered are beginning to allow the design of complex clusters with desired properties and structures and several structural types and novel physical properties are examined. In this *critical review* the synthetic and design approaches to the many polyoxometalate cluster types are presented encompassing all the sub-types of polyoxometalates including, isopolyoxometalates, heteropolyoxometalates, and reduced molybdenum blue systems. As well as the fundamental structure and bonding aspects, the final section is devoted to discussing these clusters in the context of contemporary and emerging interdisciplinary interests from areas as diverse as anti-viral agents, biological ion transport models, and materials science.

1 Introduction

During the last few years the field of polyoxometalate (POM) chemistry has undergone a revolution fuelled by the availability of extremely fast single crystal data collection strategies. This has allowed the characterisation of ultra-large clusters that have nuclearities as high as 368 metal atoms in a single cluster molecule.^{1,2} Of course, such discoveries have only been possible thanks to the advances of the instrumentation used to collect the diffraction data coupled with the advent of cheap and powerful computing power for structure solution and refinement. Much of the interest in these molecules has arisen because such clusters represent a paradigm in discovery of systems that can be encouraged to grow from molecular to the

nanoscale.^{3,4} Their versatile nature in terms of structure, size, redox chemistry, photochemistry, and charge distribution means that polyoxometalate chemistry is arguably one of the many areas in inorganic chemistry that is developing most rapidly today. Indeed, since the special thematic issue on polyoxometalates was published in *Chemical Reviews* in 1998,⁵ nearly a decade has passed. During this time developments have continued at a rapid pace, and new areas are emerging in POM chemistry that are multidisciplinary, and exploit the great structural and electronic diversity of POM-based systems. In this review we will focus on POM chemistry emerging at these interfaces with the specific idea to place the new discoveries and concepts into context rather than exhaustive coverage of specific application areas (*e.g.* catalysis which is an extremely important area but will not be covered here explicitly—instead the reader is directed to the following excellent references⁷). This is especially important now since

WestCHEM, Department of Chemistry, The University of Glasgow, Glasgow, UK G12 8QQ. E-mail: L.Cronin@chem.gla.ac.uk

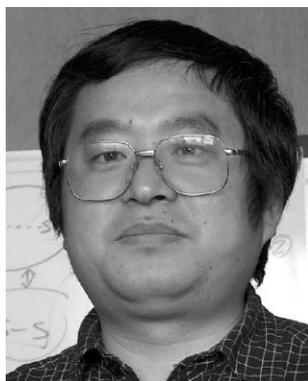

De-Liang Long

the University of Nottingham. He is currently a Research Associate in the group of Professor Lee Cronin at the University

of Glasgow. His interests are in inorganic synthesis, coordination chemistry, and cluster based materials.

De-Liang Long was born in Hunan, China. He gained his B.Sc. and M.Sc. degrees in chemistry from Wuhan University and completed his Ph.D. under the direction of Professor Xin-Quan Xin at Nanjing University in 1996. After a postdoctoral appointment at Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences, in 1999 he held the Royal Society KC Wong Fellowship working with Professor Martin Schröder at



Eric Burkholder

of Glasgow. His interests are in inorganic synthesis, coordination chemistry, and cluster based materials.

Eric Burkholder was born in Pennsylvania, USA. He gained his B.Sc. degree in chemistry from Millersville University and completed his Ph.D. under the direction of Professor Jon Zubieta at Syracuse University in 2004. He is currently a Research Associate with Professor Lee Cronin at the University of Glasgow. His

polyoxometalate chemistry continues its development, both as a pure chemical science, and also with many new dimensions in a multidisciplinary context⁶ interacting with other aspects like materials,⁸ nanotechnology,⁹ biology,^{10–13} as anti cancer, antiviral¹⁴ and even as insulin mimetic,¹³ surfaces,^{10,15} catalysis,^{16–19} supramolecular materials,^{20,21} colloid science,⁴ and electronic materials²² including electro/photo chromic systems,^{23,24} sensors,^{25,26} molecular materials^{27–29} and magnetism.³⁰

The large number of structural types in polyoxometalate chemistry³¹ can be broadly split into three classes. (i) Heteropolyanions: these are metal oxide clusters that include hetero anions such as SO_4^{2-} , PO_4^{3-} . These represent by far the most explored subset of POM clusters with over 5000 papers being reported on these compounds during the last four years alone. Much of this research has examined the catalytic properties of POMs with great emphasis on the Keggin $\{\text{XM}_{12}\text{O}_{40}\}$ and the Wells–Dawson $\{\text{X}_2\text{M}_{18}\text{O}_{62}\}$ (where M = W or Mo and X = a tetrahedral template) anions which represent the archetypal systems. In particular W-based POMs are robust and this has been exploited to develop W-based Keggin ions with vacancies that can be systematically linked using electrophiles to larger aggregates.³² (ii) Isopolyanions: these are composed of a metal-oxide framework, but without the internal heteroatom/heteroanion. As a result, they are often much more unstable than their heteropolyanion counterparts.³³ However they also have interesting physical properties such as high charges and strongly basic oxygen surfaces which means they are attractive units for use as building blocks.⁹ (iii)



Leroy Cronin

Lee Cronin graduated with a first class honours degree in Chemistry in 1994 from the University of York, and obtained a D.Phil. in bio-inorganic chemistry in 1997 at the University of York under the supervision of Prof. P. H. Walton. In October 1997 he moved to the University of Edinburgh to take up a postdoctoral fellowship with Dr N. Robertson in macrocyclic ligand design and in the summer of 1998, he took a two-month leave-of-absence

to work at the University of Hokkaido, Japan, Institute of Electronic Science with Prof. T. Nakamura in the area of molecular conductors and magnetism. In August 1999 he began an Alexander von Humboldt Research Fellowship with Prof. A. Müller at the University of Bielefeld in Germany on the synthesis and crystallographic analysis of very large polyoxometalate clusters. He then started his independent academic career in 2000 where he was appointed to a lectureship at the University of Birmingham. In 2002 he moved to take up a Lectureship in Glasgow and was promoted to Reader in 2005 and to Full Professor in 2006, and he was recently awarded a five year EPSRC Advanced Research Fellowship. He has wide ranging research interests presently focusing in cluster chemistry, ligand design and supramolecular chemistry. In particular he is interested in assembling functional nanosystems and has an interest in chemical complexity.

Mo-blue and Mo-brown reduced POM clusters: these are related to molybdenum blue type species, which was first reported by Scheele in 1783.³⁴ Their composition was largely unknown until Müller *et al.* reported, in 1995, the synthesis and structural characterisation of a very high nuclearity cluster $\{\text{Mo}_{154}\}$ crystallised from a solution of Mo-blue, which has a ring topology.¹ Changing the pH and increasing the amount of reducing agent along with incorporation of a ligand like acetate facilitates the formation of a $\{\text{Mo}_{132}\}$ spherical ball-like cluster³⁵ and therefore this class of highly reduced POM clusters represents one of the most exciting developments in POM chemistry and with many potential spin off applications in nanoscience.

2 Synthetic strategies

Before outlining the general approach to the synthesis of POM clusters it is informative to *consider the most useful synthetic approaches reported* for derivatisation and functionalisation of fragments leading to a huge variety of structures. These include (i) the potential of the system to generate a versatile library of linkable units, (ii) the ability to generate intermediates with high free enthalpy to drive polymerisation or growth processes, (iii) the possibility for structural change in the building units or blocks, (iv) the ability to include heterometallic centres in the fragments, (v) the possibility to form larger groups which can be linked in different ways, (vi) the ability to control the structure-forming processes using templates, (vii) the ability to generate structural defects in reaction intermediates (*e.g.* leading to lacunary structures) *e.g.* by removing building blocks from (large) intermediates due to the presence of appropriate reactants, (viii) the ability to localise and delocalise electrons, (ix) the ability to control and vary the charge of building blocks. In this context it is important to realise that the most stable product in the polymerisation of metal oxo-buildings is the metal oxide itself, see Fig. 1.

Generally, the approaches used to produce high nuclearity POM based clusters are extremely simple, consisting of acidifying an aqueous solution containing the relevant metal oxide anions (molybdate, tungstate and vanadate). In the case of acidification, for example, a solution of sodium molybdate will give rise to metal oxide fragments, which increase in nuclearity as the pH of the solution decreases.^{6,37}

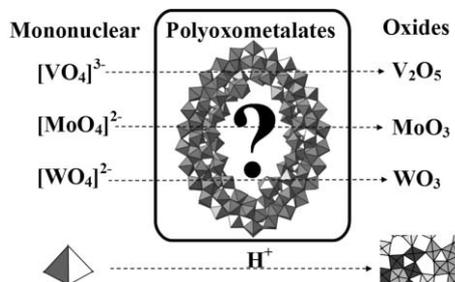


Fig. 1 Polyoxometalates are formed in experimental conditions that allow linking of polyhedra. Discrete structures are formed as long as the system is not driven all the way to the oxide. One such example, in this case a part of a $\{\text{Mo}_{256}\text{Eu}_8\}$ cluster unit,³⁶ is depicted in the square.

These isopolyanions have been extremely well investigated in the case of molybdenum, vanadium and tungsten. However, the tungsten cases are limited due to the time required for the system to equilibrate (of the order of weeks).³⁷ Heteropolyanions are another class of cluster that can be synthesised when hetero atoms are introduced, and these are extremely versatile. Indeed, heteroanions based on tungsten have been used in the assembly of extremely large clusters.³² In the case of molybdenum the acidification of solutions of molybdate followed by its subsequent reduction yields new classes of clusters with interesting topologies and very large nuclearities.^{1,35} The synthetic variables of greatest importance in synthesising such clusters are (i) concentration/type of metal oxide anion, (ii) pH and type of acid, (iii) type and concentration of electrolyte, (iv) heteroatom concentration, (v) possibility to introduce additional ligands, (vi) reducing agent (particularly in the case of the Mo systems), (vii) and other basic parameters such as temperature and solvent. Often such syntheses are done in a single pot and this can mask the extraordinary complexity of the assembly event(s) that results with the high nuclearity cluster. As we continue through this review specific reaction variables and considerations will be pointed out in the relevant sections.

In addition to traditional POM syntheses that were normally carried out in aqueous solution at room temperature or at elevated temperatures not higher than the boiling point of the solvent, synthetic strategies based on a hydrothermal approach have been developed recently and this method has been widely applied in the synthesis of POM clusters.³⁸ A few new interesting structures were reported recently. For example, a novel three-dimensional framework formed by $[\text{GdMo}_{12}\text{O}_{42}]^{9-}$ anions with nine coordinated Gd(III) centres was discovered by Wu *et al.*³⁹ and a three-electron reduced heteropoly blue $[\text{P}_6\text{Mo}_{18}\text{O}_{73}]^{11-}$ with a basket-shaped skeleton was reported;⁴⁰ this is structurally similar to that of a Dawson structure, but expanded with extra phosphate anions on the shell of the cluster along with a coordinated potassium ion, see Fig. 2.

3 New structure types

3.1 Isopolyanions

Until now only a few (*ca.* 30) isopolyanions were known and only a few examples have been reported during the last couple of years. For example, Pope *et al* reported the characterisation of the formation of unsymmetrical polyoxotungstates *via* transfer of POM building blocks. Indeed, NMR studies support the kinetic stability of the pentatungstate anion, $[\text{W}_5\text{O}_{18}]^{6-}$, in aqueous solution.⁴¹ A $\{\text{W}_{24}\}$ isopolyoxotungstate $\text{Cs}_{24}(\text{W}_{24}\text{O}_{84})(\text{H}_2\text{O})_{26}$ was reported by Bruedgam *et al.*⁴² which has a ring structure based around a six-fold axis. Not only is it made up of WO_6 octahedra, but it also contains WO_5 units, which are very rare. Six vertex-sharing WO_6 octahedra form an inner ring and six W_3O_{13} groups are condensed to this ring, again through common octahedral vertices. Also, the W_3O_{13} groups are made up of two vertex-sharing octahedral WO_6 and one pyramidal WO_5 , which is distorted in the direction of a trigonal bipyramid, see Fig. 3.

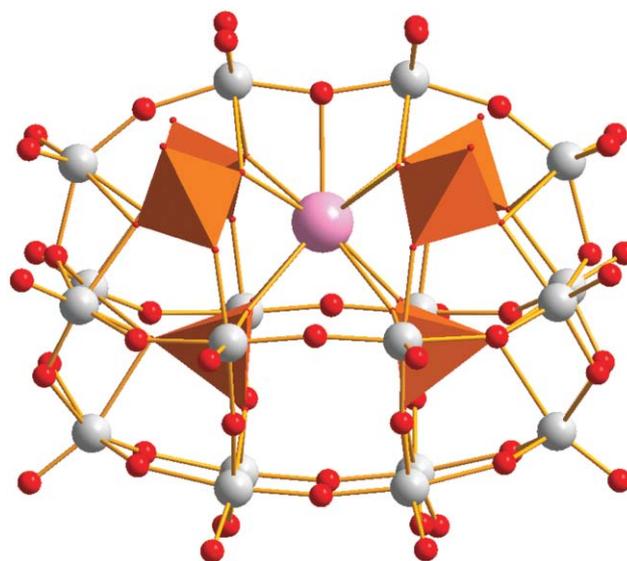


Fig. 2 A representation of $[\text{Kc}(\text{P}_6\text{Mo}_{18}\text{O}_{73})]^{10-}$. Colour scheme: Mo, grey; K, purple; O, red. PO_4 moieties are shown as orange tetrahedra.

Conventionally, POMs are normally synthesised and isolated using simple counterions such as Na^+ , K^+ , and NH_4^+ and organic tetraalkylammonium cations. Some years ago, through our research, we realised that protonated organic amines with hydroxyl groups can be used as cations and pH buffer systems and could *manipulate* the assembly of the overall POM, especially for Mo and W systems (these could even be thought of as inverse templates in contrast to the templating role of organo-amines in the formation of certain aluminosilicates and aluminophosphates; the structures of these amines can even be used in the *de novo* design of such

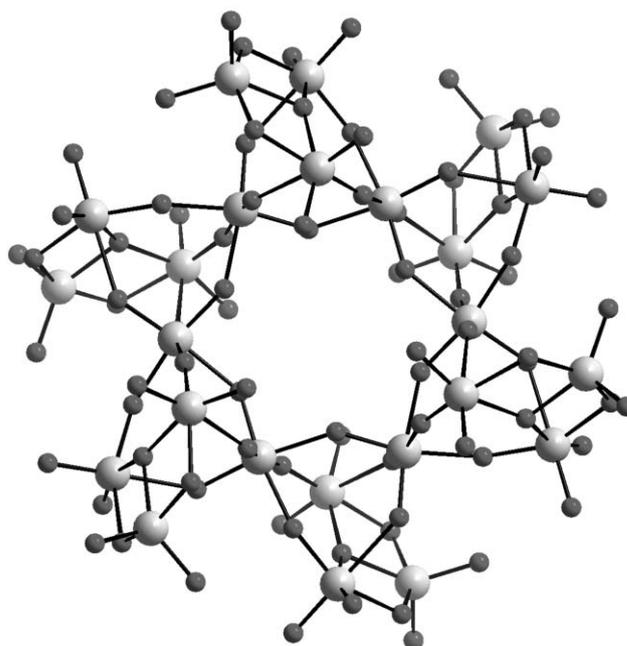


Fig. 3 A representation of the six-fold structure of the cluster $[\text{W}_{24}\text{O}_{84}]^{24-}$. Colour scheme: W, light grey; O, dark grey.

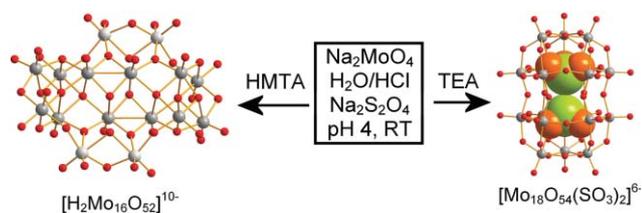


Fig. 4 Illustration of cation effect on the formation of POM clusters. Colour scheme: Mo, grey; O, red or orange; S, green. The SO_3 moieties are shown in a space filling representation.

materials).⁴³ For vanadate systems, the use of protonated organic amines as cations is limited as the pH for polyoxovanadate formation is most often around neutral or higher and at these pH values organic amines are unlikely to be protonated. Therefore protonated hexamethylenetetraamine (HMTAH^+ or $\text{C}_6\text{H}_{13}\text{N}_4^+$) was primarily utilised in our work on the synthesis of polyoxomolybdates at pH 4, which led to the isolation of quasi-stable clusters such as $[\text{H}_2\text{Mo}_{16}\text{O}_{52}]^{10-}$, see Fig. 4.⁴⁴ This cluster has been found to have a flat geometry and four of the 16 molybdenum centres are one electron reduced. The shape of the cluster resembles that of a ‘bat’ and its main ‘body’ consists of a central unit with twelve molybdenum atoms and two ‘wings’ each with two molybdenum atoms (giving the formulation $[\text{Mo}_{12} + 2\text{Mo}_2]$). In contrast to known polyoxomolybdates of similar nuclearity, $[\text{H}_2\text{Mo}_{16}\text{O}_{52}]^{10-}$ has a flat form with dimensions of *ca.* $13 \text{ \AA} \times 11 \text{ \AA} \times 6 \text{ \AA}$. Of the twelve molybdenum centres that form the main body of the ‘bat’, eight molybdenum centres are placed in two lines of four to form two $[\text{Mo}_4]$ ‘backbones’. The two protons in the $[\text{H}_2\text{Mo}^{\text{V}}_4\text{Mo}^{\text{VI}}_{12}\text{O}_{52}]^{10-}$ anion are involved in the hydrogen bonding interactions inside the cluster ($\text{O}\cdots\text{O}$ distance of $2.732(5) \text{ \AA}$).

The anion $[\text{H}_2\text{Mo}^{\text{V}}_4\text{Mo}^{\text{VI}}_{12}\text{O}_{52}]^{10-}$ demonstrates a high nucleophilicity and is capable of binding divalent transition metal ions (Fe^{II} , Mn^{II} , Co^{II} , Ni^{II} , or Zn^{II}) into its framework. This yields a family of isostructural complexes and shows the basic topology found for the $[\text{H}_2\text{Mo}^{\text{V}}_4\text{Mo}^{\text{VI}}_{12}\text{O}_{52}]^{10-}$ cluster with the addition of two $[\text{M}^{\text{II}}(\text{H}_2\text{O})_4]$ moieties yielding a complex of the composition: $[\text{M}^{\text{II}}_2(\text{H}_2\text{O})_8\text{H}_2\text{Mo}^{\text{V}}_4\text{Mo}^{\text{VI}}_{12}\text{O}_{52}]^{6-}$ ($\text{M} = \text{Mn}, \text{Fe}, \text{Co}$).⁴⁵

While $[\text{H}_2\text{Mo}^{\text{V}}_4\text{Mo}^{\text{VI}}_{12}\text{O}_{52}]^{10-}$ is diamagnetic because of strong antiferromagnetic exchange within each of the two pairs of Mo^{V}_2 units, (with $\chi_{\text{dia/TIP}} = -1.1 \times 10^{-3} \text{ emu mol}^{-1}$), the magnetic properties of the complexes $[\text{M}_2(\text{H}_2\text{O})_8\text{H}_2\text{Mo}^{\text{V}}_4\text{Mo}^{\text{VI}}_{12}\text{O}_{52}]^{6-}$ ($\text{M} = \text{Fe}, \text{Mn}$ and Co) indicate weak, yet significant, intramolecular antiferromagnetic exchange interactions between the two M^{II} centres despite their wide spatial separation of 1.18 nm. This exemplifies the efficiency of reduced polyoxomolybdates to act as superexchange ligands, where in the present case the superexchange pathways involve at least six centres and both $[\text{Mo}^{\text{V}}_2]$ dimers of the $[\text{Mo}_{12}]$ framework. The encapsulation of the cluster anion also effectively prevents any significant inter-cluster exchange interactions.

Extending the synthetic strategy utilising organo cations to a tungsten system with protonated triethanolamine (TEAH^+), led to the isolation of a new isopolytungstate

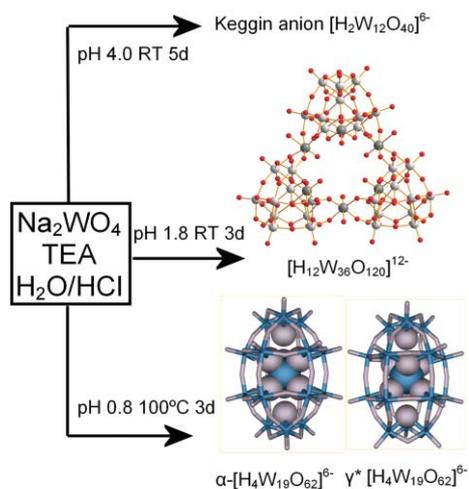


Fig. 5 Summary of pH effect on the system of tungstate and TEA. Colour scheme: W, grey (the six basal W atoms in the W_{36} are shown as larger spheres) or blue; O, red or purple.

$[\text{H}_{12}\text{W}_{36}\text{O}_{120}]^{12-}$ with an alkali or alkaline earth metal ion to form metal complexes of the type $\{\text{MCW}_{36}\}$ ($\text{M} = \text{K}^+, \text{Rb}^+, \text{Cs}^+, \text{NH}_4^+, \text{Sr}^{2+}$ and Ba^{2+}), see Fig. 5.^{46,47} The $\{\text{MCW}_{36}\}$ clusters are approximately C_{3v} -symmetric with a Celtic ring-like shape and comprise three $\{\text{W}_{11}\}$ cluster subunits linked together by three $\{\text{W}_1\}$ bridges, see Fig. 5. The $\{\text{W}_{11}\}$ cluster consists of a ring of six basal W positions, an additional W position in the centre of this ring, and four apical W positions in a butterfly configuration. Within the $\{\text{W}_{11}\}$ moieties, two protons form hydrogen bonds between the four central $\mu_{3/4}$ -oxo ligands which are visible in ^1H NMR at 5.2–5.6 ppm. The M^{n+} ion ($\text{M} = \text{K}^+, \text{Rb}^+, \text{Cs}^+, \text{Sr}^{2+}$ and Ba^{2+}) located at the cluster centre has a rather distorted coordination geometry and is coordinated by 10 oxygen atoms, of which six are from the $\text{O}_{\text{terminal}}$ ligands of the $\{\text{W}_{36}\}$ cluster and four are water ligands.

Most recently we discovered a new family of isopolyoxotungstate $[\text{H}_4\text{W}_{19}\text{O}_{62}]^{6-}$, which was isolated in a similar system to that for $\{\text{W}_{36}\}$ clusters using TEAH^+ as cations with only slightly lower solution pH and longer heating time.⁴⁸ Two isomers α - and γ^* - $[\text{H}_4\text{W}_{19}\text{O}_{62}]^{6-}$ were obtained and characterised crystallographically; the α form has D_{3h} symmetry and the γ^* form D_{3d} symmetry. The α - $[\text{H}_4\text{W}_{19}\text{O}_{62}]^{6-}$ comprises the $\{\text{W}_{18}\text{O}_{54}\}$ cage framework and interior oxo ligand positions of the conventional Dawson cluster anion α - $[\text{W}_{18}\text{O}_{54}(\text{XO}_4)_2]^{n-}$ but, contrary to the classical Dawson structure, the two tetrahedral heteroanions are replaced by a triangular-prismatic $\{\text{WO}_6\}$ unit and two μ_3 -oxo ligands, each of which bridges the capping $\{\text{W}_3\}$ triangle from inside the cluster. Two tetrahedral ‘voids’ are identified at the positions that are typically occupied by the heteroatoms in conventional Dawson cluster anions α - $[\text{W}_{18}\text{O}_{54}(\text{XO}_4)_2]^{n-}$. The γ^* - $[\text{H}_4\text{W}_{19}\text{O}_{62}]^{6-}$ is based on the geometry of the $\{\text{W}_{18}\text{O}_{54}\}$ cage framework and interior oxo ligands, as found in the conventional Dawson cluster anion γ^* - $[\text{W}_{18}\text{O}_{54}(\text{SO}_4)_2]^{4-}$.¹⁹ Again, an additional W position is located at the centre of the cluster and coordinates to six oxo ligands to form a central $\{\text{WO}_6\}$ centrosymmetric template of octahedral geometry, see Fig. 5.

One interesting observation we have made in all the work done utilising the TEAH⁺ cations, as summarised in Fig. 5, is that clusters with 3-fold symmetry are exclusively produced from the reaction systems. These observations may be completely circumstantial, but we have isolated over 4 distinct structure types using the TEAH⁺ cations, and this has led us to propose that the TEAH⁺ cation is able to transfer its symmetry onto the clusters in solution. Indeed, supramolecular interactions between the TEAH⁺ cation and the cluster building blocks *via* the three hydroxyl groups on the TEAH⁺ cation, can form H-bonds to intermediate components of the final product and possibly even guide their assembly to the overall cluster architecture.⁴⁸ In addition, this hypothesis is supported by the observation that a similar reaction, which produces 3-fold symmetric [Mo₁₈O₅₄(SO₃)₂]⁶⁻ clusters in the presence of TEAH⁺, yields low symmetrical-type POM clusters of [H₂Mo₁₆O₅₂]¹⁰⁻ with different large cations, *e.g.* protonated hexamethylenetetramine, see Fig. 3.

3.2 Non-conventional Dawson-type clusters

Conventional Dawson-type clusters contain two tetrahedral templates (XO₄). There are two kinds of non-conventional Dawson-type clusters: one is where the two tetrahedral templates (XO₄) are replaced by one or two triangular pyramid templates (XO₃) and the other is where one X atom is missing in the conventional Dawson-type clusters. In the first case the X atoms have been known for As, Sb, Bi prior to 2000.⁴⁹ Recently examples for Sn have been reported in the cluster [H₃SnW₁₈O₆₀]⁷⁻.⁵⁰ The peanut shaped cluster is a non-conventional Dawson cluster with 18 W atoms on the shell. There is only one X (As, Sb, Bi, Sn) atom disordered between two possible sites which are distant by *ca.* 2.0 Å from each other, which is obviously too short to hold two fully-occupied X atoms due to the large size of the hetero atoms As, Sb, Bi and Sn. In our work we anticipated that the inclusion of the sulfite anion into the Dawson-structure type would represent the first examples of Dawson-like cluster containing two triangular pyramid templates (XO₃).⁵¹ The first example in this series was a α -[Mo₁₈O₅₄(SO₃)₂]⁶⁻ which was isolated as a reduced cluster, produced by the reaction of sodium molybdate with reducing agent Na₂S₂O₄ in the presence of protonated triethanolamine (TEAH⁺) as cation at a pH of *ca.* 4, see Fig. 4.

This initial work was extended by the discovery of non-reduced both α - and β -[Mo₁₈O₅₄(SO₃)₂]⁴⁻, see Fig. 6.⁵¹ The [Mo₁₈O₅₄(SO₃)₂]⁴⁻ also has a peanut shape similar to that of [H₃SnW₁₈O₆₀]⁷⁻.⁵⁰ However the two encapsulated sulfur atoms are located only 3.2 Å apart from each other inside the cluster shell (this is 0.4 Å less than the 3.6 Å expected from non-bonded S...S interactions but still longer than the 2.2 Å found in S₂O₆²⁻) and could indicate a strong interaction between the two sulfur atoms; this was also suggested by DFT calculations.⁵¹ By altering the synthetic conditions we also obtained the first few examples of SO₃ based polyoxotungstates, α -[W₁₈O₅₄(SO₃)₂]⁴⁻,⁵² which is isostructural to α -[Mo₁₈O₅₄(SO₃)₂]⁴⁻,⁵¹ and [W^{VI}₁₈O₅₆(SO₃)₂(H₂O)₂]⁸⁻.⁵² The latter is described as a “Trojan Horse” in which a structural re-arrangement allows the two embedded pyramidal sulfite (SO₃²⁻) anions to release up to four electrons

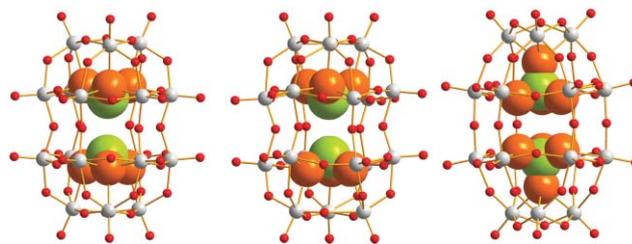


Fig. 6 Comparison of the α -SO₃- (LEFT), the β -SO₃- (MIDDLE), and the SO₄-based Dawson clusters (RIGHT) showing that the sulfur atoms of the sulfite clusters are directly adjacent. Colour scheme: O, red; Mo, grey; S, green and O of the SO₃, orange (atoms of the sulfite and sulfate anions are shown in larger spheres).

(analogous to the “soldiers” hidden inside the “Trojan Horse”) to the surface of the cluster generating the sulfate-based, deep blue, mixed valence cluster [W₁₈O₅₄(SO₄)₂]⁸⁻ upon heating, see Fig. 7. The sulfite anions adopt a radically different orientation in [W^{VI}₁₈O₅₆(SO₃)₂(H₂O)₂]⁸⁻ whereby they each only ligate to seven metal centres: three from the cap and four (out of six) from the “belt” of the cluster framework, see Fig. 7.

The orientation for the sulfite anions within the cluster type is somewhat like the coordination mode for the tetrahedral templates (XO₄^{Y-}) in conventional Dawson [M₁₈O₅₄(XO₄)₂]^{2Y-}, *i.e.* one of the oxo ligand bridges three capping W centres, the remaining oxo ligands each bridge two of the “belt” W centres. Nevertheless, this leaves two “belt” W atoms uncoordinated to the template SO₃ moiety as SO₃ has one oxo ligand less than XO₄. Thus it can be seen that the sulfite ions are grafted onto the bottom side of the cluster, which resembles a “basket” with four “uncoordinated” “belt” metal centres on the top part and now has a lower C_{2v} symmetry compared to the D_{3h} symmetric cluster α -[Mo₁₈O₅₄(SO₃)₂]⁴⁻. To compensate for the coordination, these unique “uncoordinated” “belt” W centres (four for the whole cluster) each have two terminal ligands, rather than one as found for the remaining metal centres in the cluster. These are in addition to the four other μ_2 bridging oxo (O²⁻) ligands between metal centres and complete a slightly distorted octahedral coordination geometry for each of the four “uncoordinated” “belt” metal centres concerned. Single

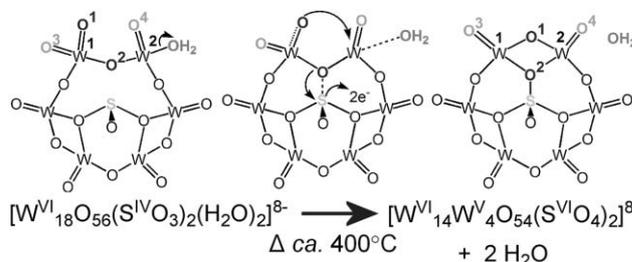


Fig. 7 Scheme showing the change in the metal oxo-framework on one half of the cluster upon oxidation of the internal SO₃²⁻ ligand to SO₄²⁻ (shown by the movement of each of the number oxygen atoms on the LHS to the end position on the RHS) which is commensurate with the reduction of the cluster shell by 4 electrons giving rise to the deep blue material from the colourless crystals.

crystal structure analysis revealed that two of the four unique metal centres each have two W=O terminals (W–O \sim 1.7 Å) and the other two each have one W=O terminal and one W–OH₂ terminal (W–O \sim 1.7 Å and \sim 2.2 Å, respectively). Furthermore it is interesting that the unique “belt” μ_2 bridging oxo ligands between the pair “uncoordinated” “belt” W atoms now bends in towards the cluster, rather than outwards as normal and is located *ca.* 2.9 Å distant from the sulfur centre of the SO₃ moiety, whilst the two sulfur centres are positioned 3.6 Å apart at opposite sides of the cluster shell. In this respect the mechanism for the reduction of the cluster shell proposes an interaction between the sulfur atom and the special belt oxo ligand, which then react to form two sulfate anions located within the {W₁₈} cluster shell, see Fig. 7.

The structure of non-conventional Dawson cluster, α -[Mo₁₈O₅₄(P₂O₇)₂]⁴⁻, has been reported by Körtz and Pope⁵³ in which the coordination of the pyrophosphate anion is quite similar to two sulfite anions in the cluster α -[Mo₁₈O₅₄(SO₃)₂]⁴⁻,⁵¹ with the only difference being that an oxygen atom is located in between two phosphorus atoms. This oxygen atom causes the structure to expand in [Mo₁₈O₅₄(P₂O₇)₂]⁴⁻ around the six equatorial oxygen atoms in the middle. The pyrophosphate anion P₂O₇⁴⁻ can be described structurally as two corner sharing tetrahedra and each P atom coordinates to the cluster shell *via* 3 oxo atoms. A cigar-shaped 30-molybdobispyrophosphate [(P₂O₇)Mo₁₅O₄₅]₂⁸⁻ was also reported recently with two P₂O₇⁴⁻ included inside the cluster.⁵⁴ The P–O–P bond angle was found to be nearly linear, and it is interesting to conceive of an extended cluster type incorporating many such templates in a row, all templating an outer metal oxo shell, since the resulting structure would resemble a metal oxide tube.

In recent years, POM chemists have noted that one of the two hetero atoms in the conventional Dawson clusters could be “removed” to form semivacant clusters; this was observed in the monolacunary Dawson-type tungstoarsenate [H₄AsW₁₇O₆₁]¹¹⁻ and its first-row transition-metal ion derivatives.⁵⁵ X-Ray determination confirmed the configuration of a semivacant Dawson polyoxotungstate skeleton in the structures of [Ce{X(H₄)W₁₇O₆₁}]₂ (X = P, As) and even indicate the probable location of internal protons. Bond valence sum calculations for these structures show that the four protons required for charge balance in all salts of the {XW₁₈} anions and their lacunary derivatives are almost certainly bound to the oxygen atoms of the empty tetrahedra.⁵⁶

3.3 Metal complexes of lacunary clusters

Metal complexes of lacuna still remain the most popular focus of POM studies. Hundreds of different types of metal complexes lacunary POMs have been reported in the last eight years. Notably Kim and Pope reported a number of dioxouranate complexes of lacunary polyoxotungstates.⁵⁷ Lacunary polyoxotungstates are an obvious choice of materials to study with respect to sequestration of radioactive waste due to the thermal stability and the radiation resistant properties of polyoxotungstates, for example, the entrapment of UO₂²⁺ cations sandwiched between two {A-PW₉O₃₄}⁹⁻ in the compound Na₁₂[Na₂(UO₂)₂(PW₉O₃₄)₂] \cdot 4.2H₂O, see

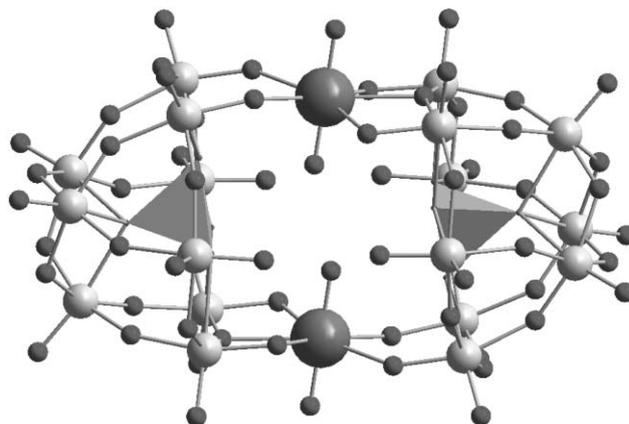


Fig. 8 A representation of the structure of [(UO₂)₂(PW₉O₃₄)₂]¹⁴⁻. Colour scheme: U, dark grey (large spheres); W, light grey; O, dark grey (small spheres). PO₄ moieties are shown as tetrahedra.

Fig. 8.⁵⁷ In addition new plenary and lacunary polyoxotungstate structures have been assembled from {As^{III}W₉O₃₃}⁹⁻ anions and uranyl cations. Since the heteropolytungstate contains AsO₃³⁻ as the templating anion, with its lone pair electrons, this prevents the formation of sandwich clusters.⁵⁸ These types of materials have led to a new structural family of heteropolytungstate lacunary complexes with the uranyl cation, UO₂²⁺, to be discovered.⁵⁹

Lanthanide complexes of lacuna-type clusters continue to yield interesting results relevant to POM chemistry and possibly even offer routes to develop new photo active and responsive materials. Many new structure types have been observed *e.g.* large cluster formation through multiple substitution with lanthanide cations (La, Ce, Nd, Sm, Eu, and Gd) of the polyoxoanion {(B- α -AsO₃W₉O₃₀)₄(WO₂)₄}²⁸⁻, and it has been shown that {(B- α -AsO₃W₉O₃₀)₄(WO₂)₄}²⁸⁻ has the ability to trap alkali, alkaline earth and lanthanide metal cations.⁶⁰ The chemistry of lanthanides with lacunary POMs is not just limited to reactions with large POM clusters. Recently, it has been demonstrated that pre-formed POMs such as {LnSiW₁₁O₃₉}⁵⁻ could readily be functionalised *via* the addition of negatively charged bridging ligands, *i.e.* acetate, where the ligand would couple two POMs by Ln–O–C–O–Ln linkages forming dimeric [(SiW₁₁O₃₉Ln)₂(μ -CH₃COO)₂]¹²⁻ (Ln = Gd^{III}, Yb^{III}) complexes.^{61,62}

Along with the f-block elements, there are a considerable number of reports based on reactions of 2nd and 3rd row d-block transition metal complexes of Pd, Pt, Ru, Rh with POM clusters, which are attractive due to potential catalytic properties. A theoretical study by Musaev *et al* was made on the role of the central template atom in the structure and reactivity of POMs with adjacent d-electron metal sites in the structure γ -[(Xⁿ⁺O₄)Ru^{III}₂(OH)₂M₁₀O₃₂]⁽⁸⁻ⁿ⁾⁻ for M = Mo and W, and X = Al^{III}, Si^{IV}, P^V, and S^{VI}.⁶³ In the study both X and M were analysed for their role in defining electronic states and reactive species. It was shown that the identity of X does significantly impact the lower lying electronic states of POMs and therefore has an important role in determining catalytic activity as it could possibly be used to ‘tune’ catalytic activity. Along with theoretical studies, several Ru–POMs have been

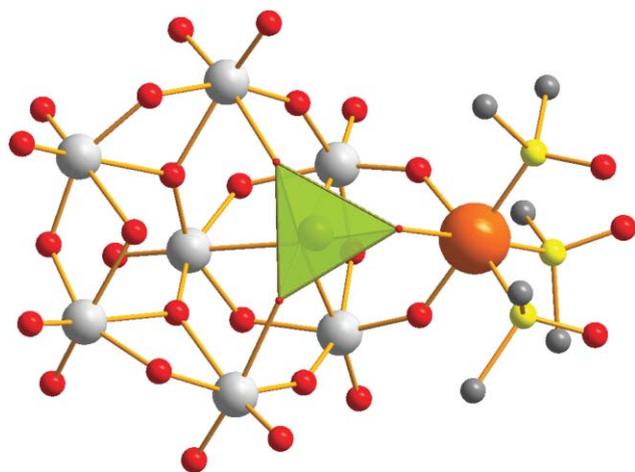


Fig. 9 A representation of the structure of $[\text{HASW}_7\text{O}_{28}\text{-Ru}(\text{dmsO})_3]^{6-}$. Colour scheme: W, grey; Ru, orange; S, yellow; O, red; C, deep grey. AsO_4 moiety is shown as a tetrahedron.

fully characterised since detailed structural understanding of pre-catalyst and active catalyst is essential for the advancement of mechanistic chemistry. The Ru-supported heteropolyanions $[\text{HXW}_7\text{O}_{28}\text{-Ru}(\text{dmsO})_3]^{6-}$ ($\text{X} = \text{P}, \text{As}$) are composed of a $\text{Ru}(\text{dmsO})_3$ group attached to an unique heptatungstate fragment *via* a facile interaction with the cluster, see Fig. 9. The Ru atom is bound to the anion by two terminal $\text{O}=\text{W}$ bonds and one $\text{O}-\text{X}$ bond, which represents a fundamentally novel mode of Ru-coordination to a polyoxoanion framework and multinuclear ^{183}W , ^{31}P , ^{13}C , with ^1H NMR studies indicating the high stability of these Ru-POMs in solution.⁶⁴

The first structurally characterised Pd-substituted tungstosilicate was $[\text{C}_8\text{K}(\text{H}_2\text{O})_7\text{Pd}_2\text{WO}(\text{H}_2\text{O})(\text{A}-\alpha\text{-SiW}_9\text{O}_{34})_2]^{9-}$, which consists of two ($\text{A}-\alpha\text{-SiW}_9\text{O}_{34}$) Keggin moieties linked *via* a $\{\text{WO}(\text{H}_2\text{O})\}^{4+}$ group and two equivalent, square-planar Pd^{2+} ions leading to a sandwich-type structure with C_{2v} symmetry. The central belt of the structure contains also one potassium and two caesium ions.⁶⁵ Some other examples of Pd-POM complexes are well described in the palladium(II)-substituted, lone pair containing tungstoarsenates(III) $[\text{Na}_2(\text{H}_2\text{O})_2\text{PdWO}(\text{H}_2\text{O})(\alpha\text{-AsW}_9\text{O}_{33})_2]^{10-}$ and $[\text{CS}_2\text{Na}(\text{H}_2\text{O})_8\text{-Pd}_3(\alpha\text{-AsW}_9\text{O}_{33})_2]^{9-}$.⁶⁶ Some other examples of large POM clusters are well demonstrated in $[(\text{As}_6\text{W}_{65}\text{O}_{217})(\text{H}_2\text{O})_7]^{26-}$.⁶⁷ In a very interesting development a late-transition metal oxo complex: $[\text{O}=\text{Pt}^{\text{IV}}(\text{H}_2\text{O})\text{L}_2]^{16-}$ has been discovered where $\text{L} = [\text{PW}_9\text{O}_{34}]^{9-}$, and this is the first complex to include a $\text{Pt}=\text{O}$ moiety,⁶⁸ see Fig. 10. Furthermore, a second cluster containing the $\text{Pd}=\text{O}$ moiety, $[\text{Pd}^{\text{IV}}\text{O}(\text{OH})\text{WO}(\text{OH}_2)(\text{PW}_9\text{O}_{34})_2]^{13-}$ was also reported,⁶⁹ in which the coordination geometry around the Pd centre is described as a distorted octahedron with five Pd-O bond distances of *ca.* 1.96 Å and one Pd=O bond distance of *ca.* 1.68 Å.

In recent years the coordination chemistry of the hexavacant tungstophosphate $[\text{H}_2\text{P}_2\text{W}_{12}\text{O}_{48}]^{12-}$ has been very popular and promising, with three good examples reported. The first one $[\text{H}_4\text{P}_2\text{W}_{12}\text{Fe}_9\text{O}_{56}(\text{OAc})_7]^{6-}$ is the coordination compound of $[\text{H}_2\text{P}_2\text{W}_{12}\text{O}_{48}]^{12-}$ with nine Fe^{III} ions.⁷⁰ Nine iron centres are attached at the hexavacant positions of the $[\text{H}_2\text{P}_2\text{W}_{12}\text{O}_{48}]^{12-}$ and are bridged and protected by seven acetates. The second

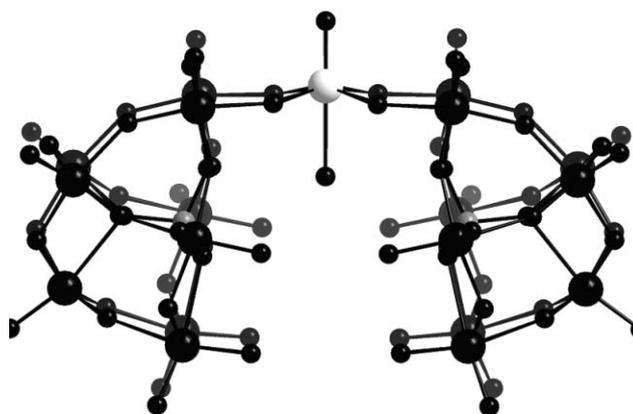


Fig. 10 The structure of the $[\text{O}=\text{Pt}^{\text{IV}}(\text{H}_2\text{O})(\text{PW}_9\text{O}_{34})]^{16-}$ complex. W = large black spheres, O = small black spheres, Pt = white, P = grey. Note the oxo ligand of the $\text{Pt}=\text{O}$ unit is assigned to the oxo site above the Pt ion whereas the site in the 'cavity' is assigned as water.

one is $[\text{H}_{12}\text{P}_4\text{W}_{28}\text{Fe}_8\text{O}_{120}]^{16-}$, which includes four iron centres located in the cluster vacancies, and the molecules are jointed together by $\text{Fe}-\text{O}-\text{Fe}$ bridges.⁷⁰ The wheel-shaped Cu_{20} tungstophosphate $[\text{Cu}_{20}\text{Cl}(\text{OH})_{24}(\text{H}_2\text{O})_{12}(\text{P}_8\text{W}_{48}\text{O}_{184})]^{25-}$ ion is the third example of a coordination compound of $[\text{H}_2\text{P}_2\text{W}_{12}\text{O}_{48}]^{12-}$,⁷¹ in which four $\{\text{P}_2\text{W}_{12}\}$ units form a ring and include 20 copper ions inside the cluster.

Other transition metal complexes of lacunary clusters have been also reported. One interesting example is the 15-cobalt-substituted polyoxotungstate $[\text{Co}_6(\text{H}_2\text{O})_{30}\{\text{Co}_9\text{Cl}_2(\text{OH})_3(\text{H}_2\text{O})_9(\beta\text{-SiW}_8\text{O}_{31})_3\}]^{5-}$ which has been characterized by single-crystal X-ray analysis. The trimeric polyanion has a core of nine Co^{II} ions encapsulated by three ($\beta\text{-SiW}_8\text{O}_{31}$) fragments and two Cl^- ligands. The central assembly $\{\text{Co}_9\text{Cl}_2(\text{OH})_3(\text{H}_2\text{O})_9(\beta\text{-SiW}_8\text{O}_{31})_3\}^{17-}$ is surrounded by six antenna-like Co ions.⁷²

3.4 Polyoxovanadates

An area of intense research in POM chemistry is the synthesis of polyoxovanadates that are known to have attractive chemical and physical properties pertaining to catalysis, biochemistry and advance materials science. Recently the focus in synthesis has been vanadate clusters with reduced or mixed-valence vanadium centres. To this avail one synthetic approach that has been adopted has been the one of synergy involving the introduction of organic and anion templating components. The anion is typically imbedded in the vanadate cluster, which can either be covalently or non-covalently bound to the vanadium atoms, used to generate clusters with unique topologies, as in the synthesis of $\text{Na}_6[(\text{PO}_4)\text{V}^{\text{V}}_6\text{V}^{\text{IV}}_{12}\text{O}_{39}]\cdot\text{H}_3\text{PO}_4\cdot 3\text{H}_2\text{O}$,⁷³ and $[\text{V}_{13}\text{V}^{\text{IV}}_3\text{O}_{42}(\text{Cl})]^{8-}$,⁷⁴ which are examples of covalently bonded and non-bonded anions respectively. The anionic cluster, $[(\text{PO}_4)\text{V}^{\text{V}}_6\text{V}^{\text{IV}}_{12}\text{O}_{39}]^{3-}$, is similar to other molecular polyoxovanadates encapsulating a VO_4 template with six $\{\text{VO}_5\}$ square pyramids and 14 octahedral $\{\text{VO}_6\}$ units. However, in contrast to other molecular clusters, the $[(\text{PO}_4)\text{V}^{\text{V}}_6\text{V}^{\text{IV}}_{12}\text{O}_{39}]^{3-}$ clusters are connected by six linear $\text{V}-\text{O}-\text{V}$ bridges into a three-dimensional framework *via* the six $\{\text{VO}_5\}$ square pyramids, see Fig. 11.

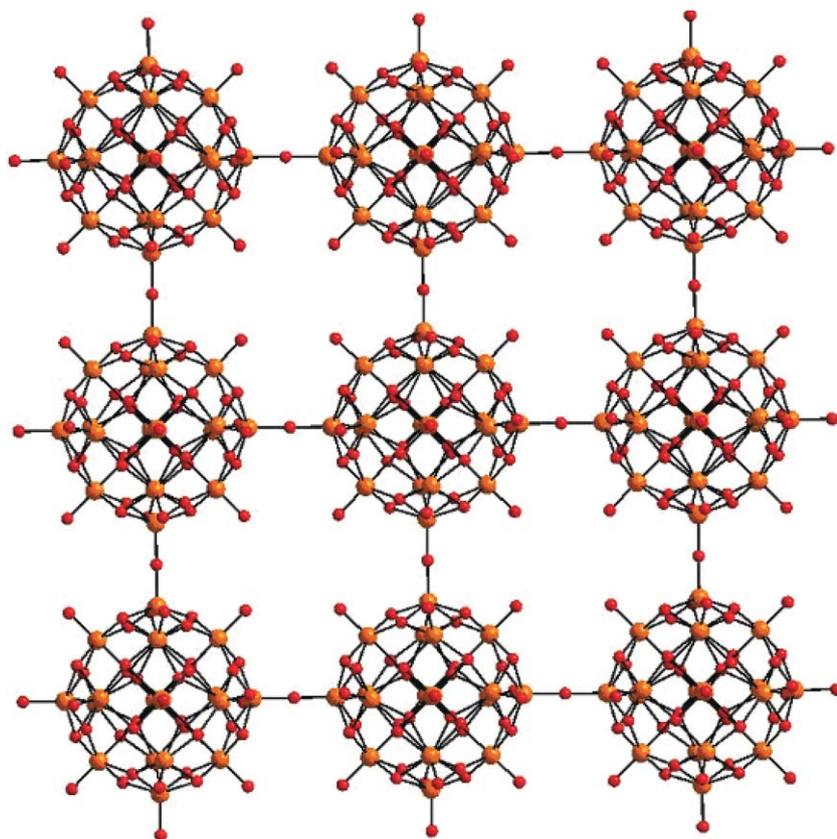


Fig. 11 Ball and stick representation of the anion network $[(\text{PO}_4)\text{V}_6\text{V}_{12}\text{O}_{39}]^{3-}$ with the sodium cation removed for clarity. Colour scheme: V, orange; P, purple; O, red. The channels of the framework are filled with sodium cations, phosphoric acid and water; interestingly the organic component, barbituric acid, was not incorporated into the structure but co-crystallized as a trimeric barbiturate salt with $\text{Na}_6[(\text{PO}_4)\text{V}_6\text{V}_{12}\text{O}_{39}]_2 \cdot \text{H}_3\text{PO}_4 \cdot 31\text{H}_2\text{O}$.⁷³

Synthesis of polyoxovanadates has classically been done in aqueous solutions or under hydrothermal conditions. Recently new synthetic routes are being explored for the formation of vanadate clusters from organic media with organically soluble vanadium precursors. One example of a vanadium cluster synthesised from organic solvent which has been reported by Hong *et al.* is $\{\text{V}^{\text{IV}}_2\text{V}^{\text{V}}_{12}\text{O}_{36}\text{Cl}\}^{5-}$ as a tetraethylamine salt that has blue luminescence.⁷⁵ In this reaction $\text{VO}_2(\text{acac})$ was used as a source of soluble VO_2^+ in acetonitrile. The cluster was then crystallised from a DMF solution with $[\text{Et}_4\text{N}]_5[\text{V}^{\text{IV}}_2\text{V}^{\text{V}}_{12}\text{O}_{36}\text{Cl}]$ being air stable in both solution and in the solid state. The cluster is built up from 14 $\{\text{VO}_5\}$ square pyramids however, unlike other polyoxovanadate clusters it is an open cage with two holes in the surface reminiscent of a basket, see Fig. 12. The non-bonded chloride anion occupies the centre of the cavity, with an average vanadium–chloride distance of 3.496 Å, and may offer a path for exchange of the chloride anion with other anions.

It would appear that polyoxovanadate chemistry still has much to offer and the move from classical aqueous solution to organic solvents *via* organically soluble vanadium precursors⁷⁵ may lead to clusters with as of yet unseen structural connectives, as well as new physical properties not previously seen in aqueous based vanadate cluster synthesis.

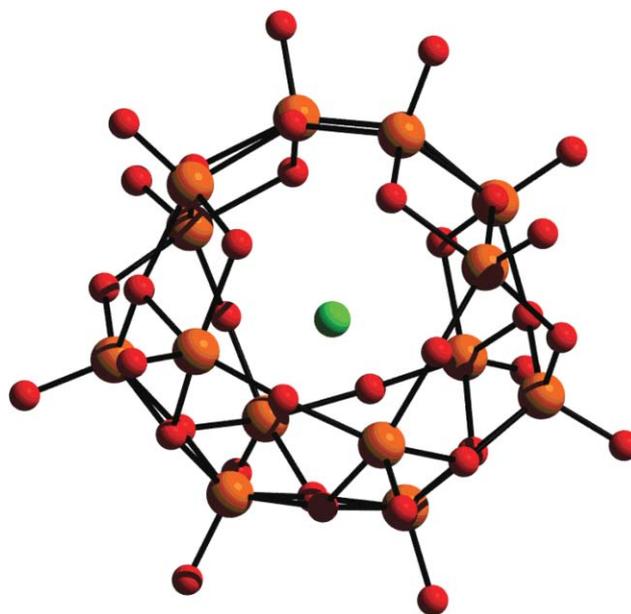


Fig. 12 Ball and stick representation of the basket $\{\text{V}^{\text{IV}}_2\text{V}^{\text{V}}_{12}\text{O}_{36}\text{Cl}\}^{5-}$ cluster with chloride in the centre. Colour scheme: V, orange; Cl, green; O, red.

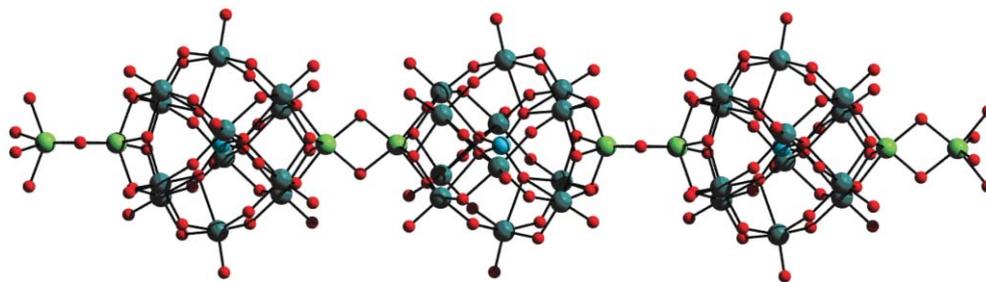


Fig. 13 View of the $\{\text{SiNb}_{12}\text{O}_{40}\}^{16-}$ and $\{\text{Ti}_2\text{O}_2\}^{4+}$ chains. Colour scheme: Nb, dark green; Ti, pale green; Si, blue; O, red.

3.5 Polyoxoniobates

Polyoxoniobate chemistry has been largely limited to isopolyoxoniobates, *i.e.* $[\text{Nb}_6\text{O}_{18}]^{8-}$ Lindqvist ion. Recently, Nyman *et al.* have developed a general synthetic protocol for the formation of heteropolyoxoniobates which has presented an important step forward since few heteropolyoxoniobates have been isolated until recently. Heteropolyoxoniobate formation is preferred in hydrothermal reaction at 170–250 °C, in aqueous alkaline mixtures.⁷⁶ The first heteropolyoxoniobate, $\text{K}_{12}[\text{Ti}_2\text{O}_2][\text{SiNb}_{12}\text{O}_{40}]$, was isolated as a Keggin ion, which is not surprising given the pervasiveness of the Keggin structure in all aspects of polyoxometalate chemistry.⁷⁶ The $\{\text{SiNb}_{12}\text{O}_{40}\}^{16-}$ cluster was isolated in the α -Keggin form linked into a one-dimensional chain by TiO_6 octahedra shown in Fig. 13.

Since the isolation of $\text{K}_{12}[\text{Ti}_2\text{O}_2][\text{SiNb}_{12}\text{O}_{40}]$ as a 1-D chain both $\text{Na}_{16}[\text{SiNb}_{12}\text{O}_{40}]$ and $\text{Na}_{16}[\text{GeNb}_{12}\text{O}_{40}]$ have since been isolated as water soluble isolated clusters.⁷⁷ These clusters, $\{\text{XNb}_{12}\text{O}_{40}\}^{16-}$ (X = Si, Ge), have the highest negative charge compared to other Keggin, and lacunary Keggin clusters with such high charge should provide these clusters with unique properties with respect to metal binding. In this context it is important to note that the first lacunary heteropolyoxoniobate, $\text{Na}_{15}[(\text{PO}_2)_3\text{PNb}_9\text{O}_{34}]\cdot 22\text{H}_2\text{O}$, which is an A-type trivacant α -Keggin cluster has also been discovered and characterised.⁷⁸

The surface of the cluster is decorated by three phosphate tetrahedra that are connected to the cluster by two corner sharing interactions with two different NbO_6 octahedra shown in Fig. 14. Each of the NbO_6 pairs that are linked by the PO_4 tetrahedra are also the same NbO_6 octahedra that edge-share in the lacuna central belt which is built up from alternating edge- and corner-sharing niobate interactions. The $\{(\text{PO}_2)_3\text{PNb}_9\text{O}_{34}\}^{15-}$ are then linked by the 15 sodium cations into a three-dimensional framework.

3.6 Mo-blue and Mo-brown clusters

Since the discovery of the $\{\text{Mo}_{154}\}$ ‘big-wheel’^{1,79} and the $\{\text{Mo}_{132}\}$ ‘big-ball’ or Kepelerate^{35,80} clusters in the late 1990’s this area of chemistry has continued to inspire chemists to both understand and utilise the unique building blocks⁸¹ present in these materials.⁸² Much progress has been made in both the wheel and ball systems including sizing of the clusters,⁸³ removal of inner building block fragments, addition of ligands, electrophiles and even promoting growth processes.^{33,80} The giant wheels represent nanosensors and nanoreactors, enabling the initiation of chemical processes at different positions, like a

“structured landscape”, and can even be used as robust synthons for the construction of compounds with typical solid-state structure, a situation comparable to crystal engineering.⁷⁹ The potential functionality of these clusters and the use of the spherical systems as functional nanospaces and models for molecular uptake and storage/as artificial cell models is discussed in section 4.4.

The reduction of molybdate in the presence of Eu(III) ions at pH 1–2 with *ca.* 20% of the added molybdate reduced to Mo(V) leads to a giant wheel shaped cluster, similar to the archetypal $\{\text{Mo}_{154}\} = [\text{Mo}_{154}\text{O}_{462}\text{H}_{14}(\text{H}_2\text{O})_{70}]^{14-}$ but this time the inclusion of the Eu(III) ions leads to the assembly of a giant elliptical cluster dimer $\{\text{Mo}_{256}\text{Eu}_8\} = \{[\text{Mo}_{128}\text{Eu}_4\text{O}_{388}\text{H}_{10}(\text{H}_2\text{O})_{81}]_2\}^{20-}$ with a diameter of *ca.* 4 nm, see Fig. 15. It appears that the inclusion of the Eu(III) ions causes a dramatic increase in curvature, when compared to the original $\{\text{Mo}_{154}\}$ wheel which results in the elliptical shape of the new cluster.³⁶

In a further dramatic development a new $\{\text{Mo}_{368}\}$ ‘lemon’ shaped cluster was synthesized with the approximate formula $[\text{H}_{16}\text{Mo}_{368}\text{O}_{1032}(\text{H}_2\text{O})_{240}(\text{SO}_4)_{48}]^{48-}$.² This cluster was synthesized from a solution acidified with sulfuric acid and this allowed the incorporation of the sulfate anion within the cluster framework that dramatically alters the cluster framework compared to the wheel type clusters which are synthesized under similar conditions.¹⁴⁶ In this case the

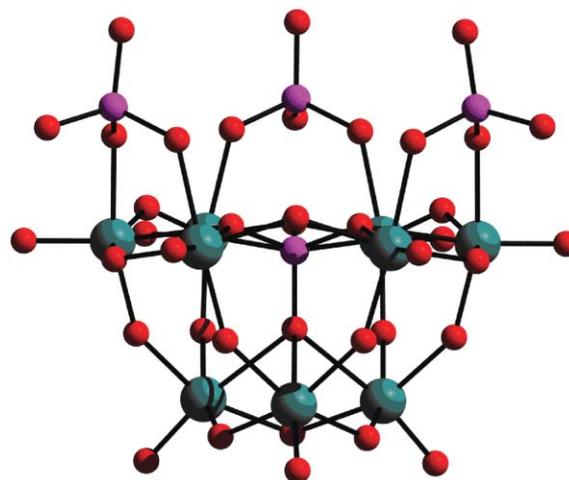


Fig. 14 View of the $\{(\text{PO}_2)_3\text{PNb}_9\text{O}_{34}\}^{15-}$ cluster showing the surface decoration by three phosphates. Colour scheme: Nb, dark green; P, purple; O, red.

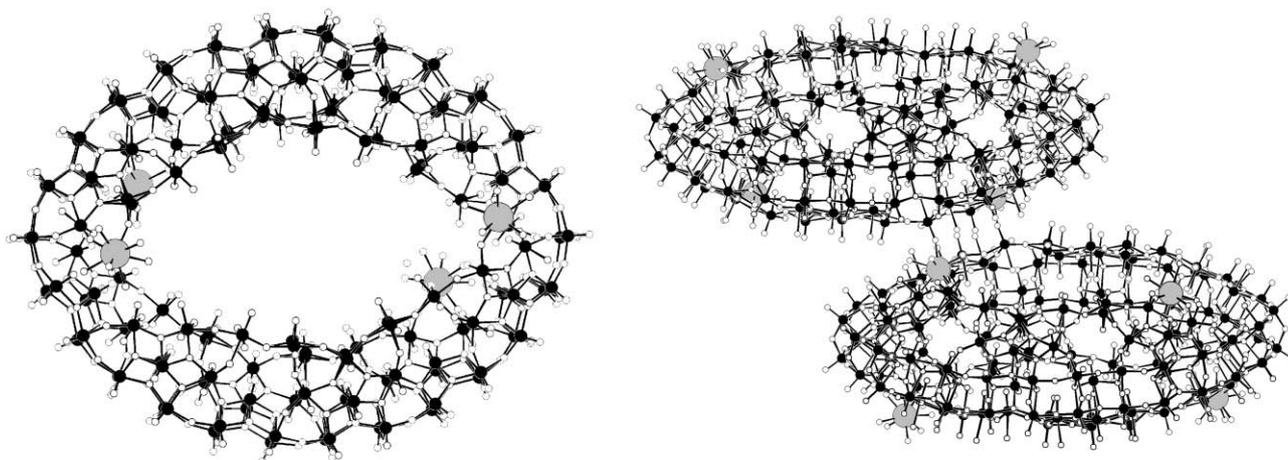


Fig. 15 The structure of the elliptical $\{\text{Mo}_{128}\text{Eu}_4\}$ wheel (LHS) and the structure of the full dimeric $\{\text{Mo}_{256}\text{Eu}_8\}$ cluster unit (RHS); the Eu(III) ions are depicted as grey spheres, Mo ions as black spheres, and oxygen atoms as white spheres.

'lemon' shaped cluster was synthesised at low pH (1–3) and with 30% of the available molybdate reduced to Mo(V). Thus the 'lemon' cluster is more highly reduced than most 'Mo-blue' species isolated to date and includes 48 sulfate anions on the inner sphere of the cluster. The cluster incorporates both positively and negatively curved surfaces and has a maximum diameter of *ca.* 5 nm, see Fig. 16.

3.7 Related building blocks

The self-condensation of $[\text{Mo}_2\text{O}_2\text{E}_2]^{2+}$ based building blocks (where E = O or S) has proved to be extremely versatile allowing a large variety of clusters, including cyclic clusters, to be isolated. In the case of the cyclic species the condensation can be performed in the presence or not of guest species. With E = O, the resulting cycles delimit an anionic open cavity, which can be filled by neutral polar molecules such as aqua ligands, or by alkaline cations. With E = S, the resulting cycles open a cationic cavity, which can be filled with neutral molecules, or anions like halides or more sophisticated groups

like carboxylates.^{84–88} For example, decavacant Dawson clusters can be linked to give a compound of the form: $[\text{Mo}_{12}\text{S}_{12}\text{O}_{12}(\text{OH})_{12}(\text{H}_2\text{O})_6]$. The $[\text{Mo}_2\text{S}_2\text{O}_2]^{2+}$ building block has been of great utility in the formation of cyclic ring clusters.⁸⁶ In addition, a polyoxothiomolybdate with a Mo^{VI} octahedron has been encapsulated in a reduced Mo–V cyclic octanuclear core⁸⁹ by self condensation of $[\text{Mo}_2\text{S}_2\text{O}_2]^{2+}$ with phosphate or arsenate ions to give $[(\text{HXO}_4)_4\text{Mo}_6\text{S}_6\text{O}_6(\text{OH})_3]^{5-}$, X = P, As.⁹⁰ The condensation of six $[\text{Mo}_2\text{S}_2\text{O}_2]^{2+}$ building blocks around the 3,5-benzenetricarboxylate anion leads to the new dodecanuclear oxothioanion $[\text{Mo}_{12}\text{S}_{12}\text{O}_{12}(\text{OH})_{12}\{\text{C}_6\text{H}_3(\text{COO})_3\}]^{3-}$, isolated as a tetramethylammonium salt and structurally characterized by single-crystal X-ray diffraction study.⁹¹ Further, the influence of a range of carboxylate anions on the self condensation process involving the $[\text{Mo}_2\text{S}_2\text{O}_2]^{2+}$ building block yields rings with 8, 10 and 12 Mo ions in a ring.⁹² The new oxothiomolybdate anion $[\text{Mo}_8\text{S}_8\text{O}_8(\text{OH})_8\{\text{HWO}_5(\text{H}_2\text{O})\}]^{3-}$ is formed from four $[\text{Mo}_2\text{S}_2\text{O}_2]^{2+}$ building blocks connected through hydroxo bridges around a central $\{\text{WO}_6\}$ octahedron.⁹³ In an

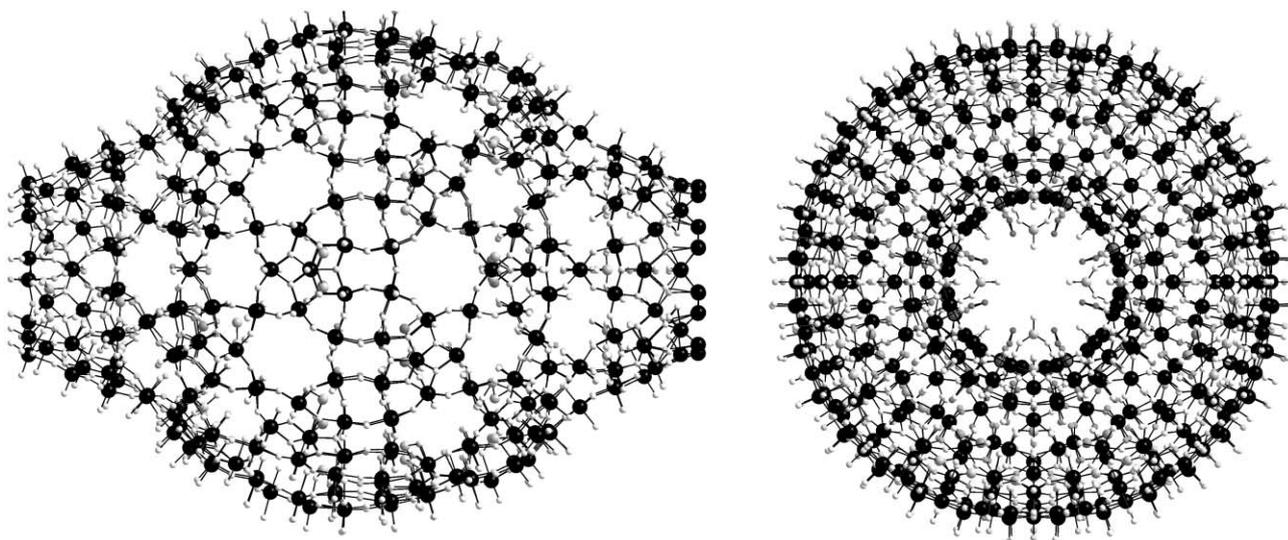


Fig. 16 The structure of the $\{\text{Mo}_{368}\}$ 'lemon' cluster. The side view is shown (LHS) and the top view is also shown (RHS).

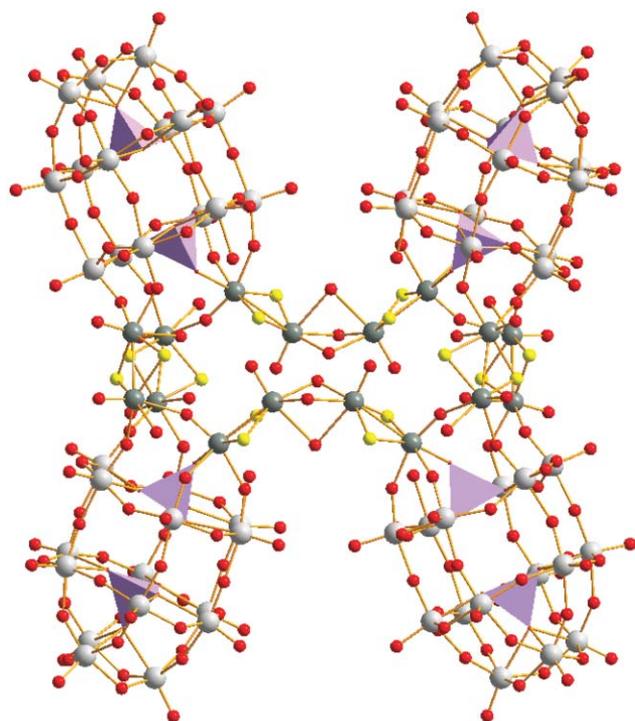


Fig. 17 A representation of the structure of $[(\alpha\text{-H}_2\text{P}_2\text{W}_{15}\text{O}_{56})_4\{\text{Mo}_2\text{O}_2\text{S}_2(\text{H}_2\text{O})_2\}_4\{\text{Mo}_4\text{S}_4\text{O}_4(\text{OH})_2(\text{H}_2\text{O})\}_2]^{28-}$. Colour scheme: W, grey; Mo, deep grey; S, yellow; O, red; PO_4 moieties are shown as pink tetrahedra.

extension of this work with $[\text{Mo}_2\text{O}_2\text{E}_2]^{2+}$ based building blocks it was shown that a supramolecular tetra-Dawson polyoxothiomolybdate: $[(\alpha\text{-H}_2\text{P}_2\text{W}_{15}\text{O}_{56})_4\{\text{Mo}_2\text{O}_2\text{S}_2(\text{H}_2\text{O})_2\}_4\{\text{Mo}_4\text{S}_4\text{O}_4(\text{OH})_2(\text{H}_2\text{O})\}_2]^{28-}$ is a polyoxothiomolybdate-based macrocycle *ca.* 3 nm in diameter which has been constructed by the connection of complementary cation fragments: $[\text{Mo}_2\text{O}_2\text{S}_2]^{2+}$ and the basic trivalent $\alpha\text{-}[\text{P}_2\text{W}_{15}\text{O}_{56}]^{12-}$ ion. The formation of Mo–OH–Mo bridges contributes to the build up of the tetrameric cluster, and shows that it is possible to generate elaborate architectures based on POM-incorporated cyclic oxothiomolybdates, see Fig. 17.⁹⁴

The sulfite anion has been utilised as an interesting building block for the formation of $[\text{Mo}_{12}\text{O}_{24}(\text{SO}_3)_{16}]^{20-}$ and $\{\text{Na}[\text{Mo}_{12}\text{O}_{24}(\text{SO}_3)_4]_2\}^{15-}$ -based framework structures.^{95,96} In addition, vanadium-based POMs of the form, $[(\text{V}^{\text{IV}}\text{O})_6(\mu_4\text{-O})_2(\mu_3\text{-OH})_2(\mu_3\text{-SO}_3)_4(\text{H}_2\text{O})_2]^{2+}$ and $[(\text{V}^{\text{IV}}\text{O})_6(\mu_4\text{-O})_2(\mu_3\text{-OH})_2(\mu_3\text{-SO}_3)_4(\text{H}_2\text{O})_2]$ have been isolated that exhibit a unique structural motif with a central cubic $\{\text{V}^{\text{IV}}_4\text{O}_2(\text{OH})_2\}$ fragment and two vanadium(IV) ions located at two of the corners of the cluster.⁹⁷ Sulfite-based heteropolyoxometalates have also been synthesised with the Dawson-like cage structure, $[\text{M}_{18}\text{O}_{56}(\text{SO}_3)]^{4-}$ ($\text{M} = \text{Mo}$ or W)⁵¹ and these and related derivatives were discussed previously in section 2.2.⁵²

4 Materials, biology, devices and nanostructures

4.1 POM-based hybrids and polymers

The derivatisation of POM frameworks by replacing/derivatising the oxo ligands is an important aim since this will allow a much greater degree of control, potentially allowing the

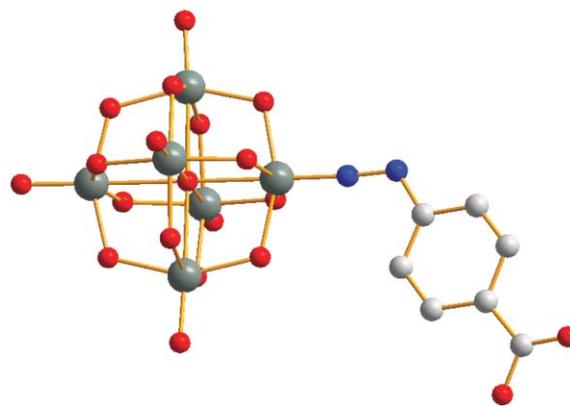


Fig. 18 Molecular structure of $[\text{Mo}_6\text{O}_{18}(\text{N}_2\text{C}_6\text{H-}p\text{-CO}_2\text{H})]^{3-}$. Colour scheme: Mo, deep grey; O, red; N, blue; C, grey.

simultaneous exploitation of self assembly of the POM fragments, and step wise synthesis to introduce pendant functionalities. One such example is the derivatisation of Lindqvist-type (aryldiazenido)polyoxomolybdates to give compounds of the form $(n\text{Bu}_4\text{N})_3[\text{Mo}_6\text{O}_{18}(\text{N}_2\text{Ar})]$, see Fig. 18.⁹⁸

Functionalisation has not only been limited to the Lindqvist but also Keggin⁹⁹ and Dawson¹⁰⁰ derivatives have been functionalised. ‘Organometallic’ POM clusters¹⁰¹ have also been produced containing Ru(*p*-cymene),¹⁰² as well as a carbene derivative of a POM, $[(\text{PW}_9\text{O}_{34})_2(\text{cis-WO}_2)(\text{cis-RuL}^{\text{Me}_2})]^{13-}$ ($\text{L}^{\text{Me}_2} = 1,3\text{-dimethylimidazolidine-2-ylidene}$).¹⁰³ Tin-based linkers can be used effectively to build complex architectures and this has been done by reacting $(\text{CH}_3)_2\text{SnCl}_2$ with $\text{Na}_9[\text{A-PW}_9\text{O}_{34}]$ to yield $\{[\text{Sn}(\text{CH}_3)_2(\text{H}_2\text{O})]_{24}\{\text{Sn}(\text{CH}_3)_2\}_{12}(\text{A-PW}_9\text{O}_{34})_{12}\}^{36-}$, see Fig. 19.¹⁰⁴

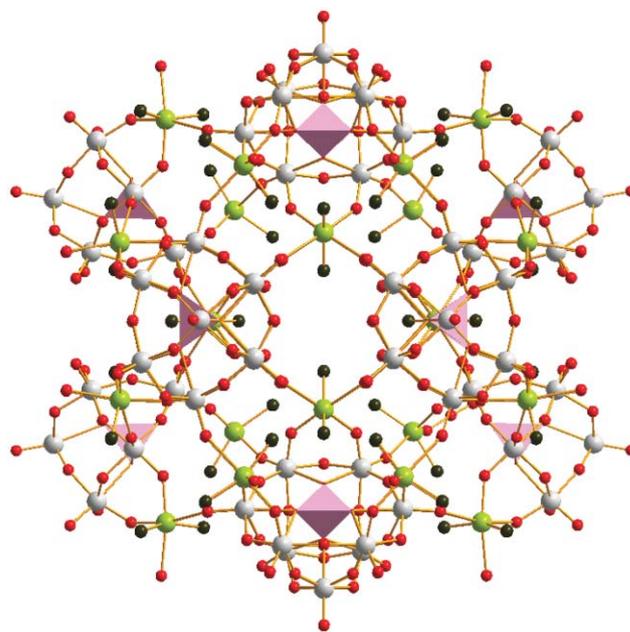


Fig. 19 A representation of the structure of $\{[\text{Sn}(\text{CH}_3)_2(\text{H}_2\text{O})]_{24}\{\text{Sn}(\text{CH}_3)_2\}_{12}(\text{A-PW}_9\text{O}_{34})_{12}\}^{36-}$. Colour scheme: W, grey; Sn, green; O, red; C, black. PO_4 moieties are shown as pink tetrahedra.

The Anderson cluster type can also be derivatised by using a ligand that has three pendant hydroxyl groups that can replace the hydroxide groups on the surface of the Anderson. This has produced a variety of tripods including 'tris' which has also allowed further derivatisation *via* imine and peptide bond formation.^{105,106}

POMs can form polymers in many ways: (i) through polymerisation by linkers of M–O–M bonds between POM clusters; (ii) covalently bonded to organic components like acetyl groups which can polymerise; (iii) covalently bonded to organic ligands like polypyridyls which can further form coordination polymers; (iv) POMs as ligands to bind metal ions to form coordination polymers.

In terms of forming direct POM polymers linked by Mo–O–Mo units, it has been observed that in the synthesis of the wheel- and sphere-shaped nanosized molybdenum-oxide based clusters even under one-pot conditions, extensive linking *via* these types of units can occur. This means that the clusters primarily formed by self-assembly can become further linked in the same phase.¹⁰⁷ An example is that the paramagnetic Keplerate "necklaces" synthesized by a novel room-temperature solid-state reaction were characterised in the solid state as metal-oxide-based nanoparticles which formed from controlled linking of $\{(Mo^{VI})-Mo^{VI}_5\}_{12}Fe_{30}$ -type Keplerate balls connected by inter-ball Mo–O–Mo bonds.¹⁰⁸

Peng's group reported a series of work on $\{Mo_6\}$ imine compounds in which POMs are covalently bonded with terpyridine ligands which can coordinate to other metal ions to form coordination polymers¹⁰⁹ and a rational synthesis of covalently bonded organic–inorganic hybrids was described.¹¹⁰ Molecular and polymeric hybrids based on covalently linked POMs and transition-metal complexes has as of yet been limited to the $Mo_6O_{19-x}(NR)_x$, $x = 1$ or 2 , cluster type.¹¹¹ POMs can also be linked through direct condensation or secondary metal ligand coordination complexes.^{112,113} Other examples of POM polymers, covalent hybrid materials based on nanolatex particles and Dawson clusters was reported recently,¹¹⁴ while coordination polymers with controllable growth of chains and grids from polyoxomolybdate building blocks linked by silver(I) dimers was demonstrated by us.¹¹⁵

POM networks are now ubiquitous, but mesoporous systems may offer some new routes to catalytic materials. For instance a mesoporous hybrid POM based on an inorganic 'sandwich' POM, $[ZnWZn_2(H_2O)_2(ZnW_9O_{34})_2]^{12-}$ with branched tripodal organic polyammonium salts has been synthesised. Electron microscopy demonstrated that a 3-D porous material was produced (3.6 nm pores) and BET measurements indicated a high surface area (30–50 m² g⁻¹). These materials behaved as very effective and selective heterogeneous catalysts for the epoxidation of allylic alcohols and oxidation of secondary alcohols to ketones with hydrogen peroxide as oxidant.¹⁶ The same 'sandwich' POM was also found to be active in the oxidation of alcohols, diols, pyridine derivatives, amines and aniline derivatives with hydrogen peroxide.¹¹⁶

4.2 POM-based materials with magnetic and conducting properties

The development of POM-based clusters incorporating paramagnetic centres is an interesting goal since it is possible to

utilise existing building blocks/clusters to generate very large magnetic molecules. In fact, it has been shown that it is possible to substitute the $\{Mo_2\}$ 'linker' groups present in the Keplerate (Pentagon)₁₂(Linker)₃₀ species with Fe^{III} to yield a $\{Mo_{72}Fe_{30}\}$ cluster with the formula $[Mo_{72}Fe_{30}O_{252}(CH_3COO)_{10}\{Mo_2O_7(H_2O)\}\{H_2Mo_2O_8(H_2O)\}_3(H_2O)_{91}]^{83}$. This cluster is smaller than the parent $\{Mo_{132}\}$ with an outer diameter of *ca.* 24 Å and inner diameter of *ca.* 18 Å. Further, the $\{Mo_{72}Fe_{30}\}$ cluster is comprised of only Mo^{VI} atoms whereas the $\{Mo_{72}Mo_{30}\}$ cluster contains 36 reduced Mo^V centres (the 30 linking units are reduced and the remaining 6 centres are delocalised over the 12 pentagonal centres present in the cluster). The presence of the Fe(III) centres, combined with the weak antiferromagnetic exchange between these centres, means that there are 30 mainly uncorrelated spins at room temperature and the cluster therefore has a very large *S* (approaching 150/2). The Fe(III) centres of the cluster span an icosidodecahedron and the extremely rich and interesting magnetic properties have been investigated using the Heisenberg model.¹¹⁷ In this respect the $\{Mo_{72}Fe_{30}\}$ has been termed as a mesoscopic paramagnet in which classical behavior extends down to extraordinarily low temperatures. Moving from Fe–Mo to Fe–Mo–V, the self-assembly of molybdate building units in the presence of Fe^{II} and V^{IV} produces the first mixed-spin heterometal Keplerate-type clusters displaying ferrimagnetic interactions¹¹⁸ where the clusters have the composition: $\{(Mo^{VI})-Mo^{VI}_5\}_{12}M_{30}$ where $M = V^{IV}, Fe^{III}$.¹¹⁹ Further, it appears that when large numbers of paramagnetic metal centres like 30 Fe^{III} or 20 VO²⁺ are integrated within their structure, extraordinary spin topologies can be realised on a discrete molecular level. Further functionalisation of these systems allows, *e.g.* to link them forming chains or layers in solid state reactions at room temperature.⁸⁰

Rather than using self assembly of pure POM building blocks, the ligand directed assembly of magnetically interesting POM clusters can also be considered. For instance a $\{V_8O_{14}\}$ cluster can be formed with two ligated 1,3,5-trideoxy-*cis*-inositol moieties yielding a vanadyl cluster with a large spin ground state arising from strong ferromagnetic interactions within the cluster. High nuclearity copper(II) complexes have been recently produced; a cavity directed $\{Cu_{20}W_{48}\}$ species, $[Cu_{20}Cl(OH)_{24}(H_2O)_{12}(P_8W_{48}O_{184})]^{25-}$ see Fig. 20 and $\{Cu_9\} = [\{SiW_8O_{31}Cu_3(OH)(H_2O)_2(N_3)\}_3-(N_3)]^{19-}$ ¹²⁰ and $\{Cu_{14}\} = \{[(SiW_9O_{34})(SiW_9O_{33}(OH))(Cu(OH))_6Cu_2]\}^{23-}$ clusters.¹²¹

The formation of hybrid materials based on POMs with stacks of partially oxidized p-electron donor molecules of tetrathiafulvalene (TTF) has been accomplished to yield conducting POM-based materials. This is interesting because the inorganic POM anion can act as a structural spacer unit, incorporate additional functionality such as a scaffold for paramagnetic ions or to act as an electron acceptor.²⁷ This area is progressing rapidly with the compounds based on $[BEDT-TTF]_5[H_3V_{10}O_{28}]^{122}$ and $[BEDT-TTF]_6[Mo_8O_{26}]^{123}$ (BEDT-TTF = bis(ethylenedithio)tetrathiafulvalene) which behave as metals down to 50 and 60 K with room temperature conductivities of 360 and 3 S cm⁻¹, respectively. In addition, a POM radical salt with metallic behavior down to 2 K has been synthesized.¹²⁴ The compound is based on

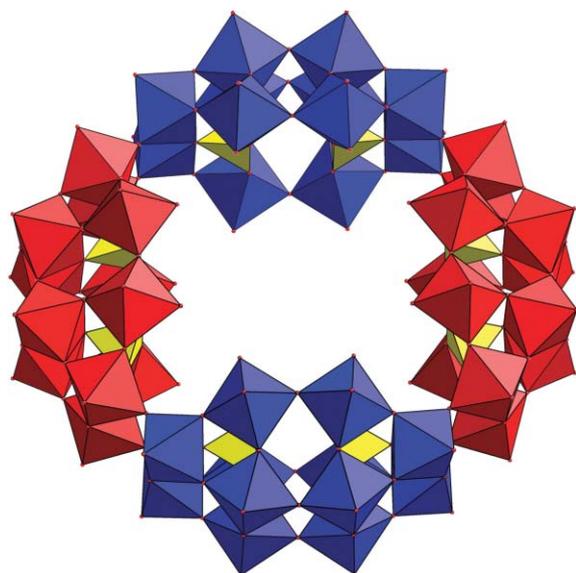


Fig. 20 Structure of the $\{W_{48}\}$ cluster showing the cavity in which the 20 copper(II) ions are complexed; the $\{W_{12}\}$ hexavacant building blocks are shown in blue and red and the copper(II) ions are omitted for clarity.

$[\text{BEDOTTF}]_6\text{K}_2[\text{BW}_{12}\text{O}_{40}]$ and is formed from $[\text{BW}_{12}\text{O}_{40}]^{5-}$ and the organic radical (BEDO-TTF) (=bis(ethylenedioxo) tetrathiafulvalene). The realization of POM–organic conducting hybrids means that devices incorporating both POM clusters and organic conductors and polymers are also accessible. A chiral POM conductor has also been produced using the chiral cluster $[\text{H}_4\text{CO}_2\text{Mo}_{10}\text{O}_{38}]^{6-}$ electrocrystallised with (BEDT-TTF or ET)²⁸ and POM-based materials that have mobile lithium ions have also been realized.⁹³

4.3 Chiral and biologically active polyoxometalates

Interest in the design and synthesis of chiral POMs has been recently gathering momentum driven by applications to materials^{125,126} and catalysis.^{127,128} The amplification and transfer of chirality from organic tartrate to a large polytungstate has been achieved by reacting the achiral lacunary Wells–Dawson POM unit, $\alpha\text{-}[\text{P}_2\text{W}_{15}\text{O}_{56}]^{12-}$, which has C_{3v} symmetry with D or L-tartrate. Given the unfavourable electrostatic interactions between these fragments a positively charged mediator, in this case, Zr^{IV} is used because of high charge and coordinative flexibility to yield the chiral POM, $\{\alpha\text{-P}_2\text{W}_{15}\text{O}_{55}(\text{H}_2\text{O})\}[\text{Zr}_3(\mu_3\text{-O})(\text{H}_2\text{O})(\text{tartH})[\alpha\text{-P}_2\text{W}_{16}\text{O}_{59}]]^{15-}$ (both enantiomers are available and depend on the symmetry ‘printed’ onto the cluster by the tart ligand). This is interesting since the cluster framework is chiral and robust, see Fig. 21. Tartrate has also been used to form POM-based chiral helical polymers with Gd(III).¹²⁹ The interaction of amino acids with enantiomers of $[\text{Ce}^{\text{III}}(\alpha\text{-P}_2\text{W}_{17}\text{O}_{61})(\text{H}_2\text{O})_x]^{7-}$ has been investigated using ³¹P NMR and shows diastereomer formation however no such splitting is observed with glycine or D/L-proline, or when chiral amino acids are added to the corresponding complex of the achiral $\alpha\text{-}[\text{P}_2\text{W}_{17}\text{O}_{61}]^{10-}$.¹³⁰

Perhaps one of the most extraordinary areas of application of polyoxometalate chemistry lies in biology,¹¹ but perhaps is

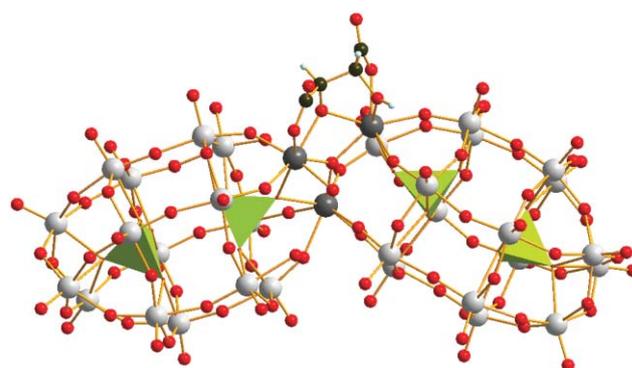


Fig. 21 A representation of the structure of $\{\alpha\text{-P}_2\text{W}_{15}\text{O}_{55}(\text{H}_2\text{O})[\text{Zr}_3(\mu_3\text{-O})(\text{H}_2\text{O})(\text{tartH})[\alpha\text{-P}_2\text{W}_{16}\text{O}_{59}]]^{15-}$. Colour scheme: W, grey; Zr, deep grey; O, red; C, black; H, light blue. The PO_4 moieties are shown as green tetrahedra.

not so surprising given the wide variety of structures, water solubility, anionic nature, electrochemical activity, and recent realisation that large inorganic clusters can penetrate cell walls. Indeed, recent investigation of anti-tumor,¹³¹ -viral, and -bacterial activities of POMs shows induced cell-apoptosis, inhibition of virus binding to a receptor, and the enhancement of P-lactam antibiotics, inhibition of bacterial growth, herbicidal action,¹³² as well as regulation of insulin levels.^{12,133} Aqueous vanadate and aqueous tungstate have been known to mimic all or most of the actions of insulin in intact cell systems with respect to normalisation of the blood glucose level.^{134,135} By carrying out oral administration *in vivo* experiments on the blood glucose level of streptozotocin (STZ)-induced diabetes (STZ mice), the insulin-mimetic (IM) effects of POMs have been examined with and without vanadium substitution. Several homo-POMs (Dawson $\{M_{18}\}$) and vanadium-substituted ($M_{16}V_2$) showed hypoglycemic effects.¹³

4.4 Polyoxometalate based nanostructure assemblies ... towards devices

The fact that POMs have high charge, well defined structures based on conserved building blocks, and form *via* self assembly means that they have great potential to bridge multiple length scales. For instance, the $\{Mo_{154}\}$ wheel cluster, self assembled at low pH under reducing conditions from Na_2MoO_4 , can undergo a further self-assembly process to form hollow spherical structures. These structures are approximately monodisperse with a radius of about 45 nm and are composed of *ca.* 1200 $\{Mo_{154}\}$ wheel-shaped clusters in solution; they appear to lie flat homogeneously distributed over a vesicle surface. Unlike conventional lipid vesicles, the structures that were observed are not stabilised by hydrophobic interactions, but rather because of a subtle interplay between short-range van der Waals attraction and long-range electrostatic repulsion, with important further stabilisation arising from hydrogen bonding involving water molecules encapsulated between the wheel-shaped clusters and in the vesicles’ interior.⁴ The cluster ball, $\{Mo_{72}Fe_{30}\}$, also undergoes a self assembly process to form hollow, 2.5-nm-diameter, spherical heteropolyoxometalate $\{Mo_{72}Fe_{30}\}$ -based macro-ions which form into single-layer vesicles (averaging 50–60 nm in diameter).¹³⁶

Large colloidal aggregates of POMs have also been used to produce 3-D nanostructures.¹³⁷

Given the anionic nature of POM clusters in general, the manipulation of POM-based materials using cation exchange is an extremely important route to the design of new materials. For instance, the partially reduced polyoxomolybdate $[\text{H}_3\text{Mo}_5\text{V}_6(\text{NO})_6\text{O}_{183}(\text{H}_2\text{O})_{18}]^{21-}$ has been encapsulated in a shell of dimethyldioctadecylammonium (DODA) surfactant molecules to give $(\text{DODA})_{20}(\text{NH}_4)[\text{H}_3\text{Mo}_5\text{V}_6(\text{NO})_6\text{O}_{183}(\text{H}_2\text{O})_{18}]$ rendering the $\{\text{Mo}_5\text{V}_6\}$ cluster core soluble in organic solvents. Slow evaporation of a solution of the surface encapsulated clusters causes the hydrophobic particles to aggregate into a cubic lattice and the compound forms stable Langmuir–Blodgett films and multilayers.¹³⁸ In an extension to this work the spontaneous self assembly of the surfactant encapsulated spherical $\{\text{Mo}_{132}\}^{42-}$ cluster has also been achieved and the nanoporous core–shell particles examined revealing a porous supramolecular structure.^{139,140} Building on this work, ultrathin composite films incorporating the $\{\text{Mo}_{132}\}^{42-}$ cluster have been constructed using a stepwise self-assembly strategy. Alternating adsorption of the Keplerate anions and PAH results in single layers with an apparent surface coverage of approximately 50%.¹⁴¹

The integration of POMs into functional architectures and devices, however, necessitates the development of general methods that allow positioning these clusters in well-defined supramolecular architectures, thin films, or mesophases. This can be done by electrostatic layer-by-layer self-assembly (ELSA) of POMs and a variety of water-soluble cationic species an also be included.²¹ Using ELSA, the formation of multilayers with polyelectrolytes and nanoscopic POM clusters of different sizes and charges has been investigated. Cyclic voltammetry indicates that the electrochemical properties of the POM clusters are fully maintained in the polyelectrolyte matrix, which opens a route toward practical applications such as sensors or heterogeneous catalysts. Also, the permeability toward electrochemically active probe molecules can be tailored through the multilayer architecture and deposition conditions.¹⁴² For instance, the POM cluster $[\text{Co}^{\text{II}}_4(\text{H}_2\text{O})_2\text{-P}_4\text{W}_{30}\text{O}_{112}]^{16-}$ embedded in a self-assembled polyelectrolyte matrix shows a remarkable pH dependence of its electrochemical response, opening a route for this material to be used as a molecular probe or to fabricate pH microelectrodes.²⁶ Biologically inspired POM–surfactant composite materials using the Keplerate cluster have also been examined¹⁴⁰ and the multilayer film composed of POM anion $\alpha\text{-}[\text{SiW}_{11}\text{O}_{39}\text{-Co}(\text{H}_2\text{PO}_4)]^{7-}$ with poly(diallyldimethylammonium chloride) was fabricated and it was shown that the film can immobilize the DNA molecules *via* a Mg^{2+} -bridging medium.¹⁰

The spherical $\{\text{Mo}_{132}\}^{42-}$ Keplerate nanocluster itself has been studied intensely recently. This cluster has the form $[\{\text{pent}_{12}(\text{link})_{30}\}]$, *e.g.* like $[\{(\text{Mo})(\text{Mo}_5\text{O}_{21}(\text{H}_2\text{O})_6)_{12}\text{-}\{\text{Mo}_2\text{O}_4(\text{ligand})\}_{30}\}^{n-}]$ with binuclear linkers where the 12 central pentagonal units span an icosahedron and the linkers are a distorted truncated icosahedron; the highly charged capsule with sulfate ligands and $n = 72$ was used very successfully. For instance, the truly nanoscale capsules (inner cavity diameter *ca.* 2.5 nm) allow different types of encapsulations, *e.g.* of well-structured large water assemblies (up to

100 molecules) with an ‘onion’ like layer structure enforced by the outer shell.^{33,143} Most importantly, the capsules have 20 well-defined pores and the internal shell functionalities can be tuned precisely since the nature of the bidentate ligands can be varied. In the special case of binuclear $\text{Mo}^{\text{V}}_2\text{O}_4^{2+}$ linkers the pores are $\{\text{Mo}_9\text{O}_9\}$ rings with a crown-ether function (diameters 0.6–0.8 nm) which can be reversibly closed, *e.g.* by guanidinium cations non-covalently interacting with the rings *via* formation of hydrogen bonds.¹⁴⁴ In a related smaller capsule with mononuclear linkers the $\{\text{Mo}_6\text{O}_6\}$ pores can get closed/complexed correspondingly by smaller potassium ions.¹⁴⁵

The most intriguing and exciting property of the highly negatively charged capsules is that they can mediate cation transfer from the solution to the inner nanocavity. Indeed, reaction of the above-mentioned highly charged capsule with different substrates/cations such as Na^+ , Cs^+ , Ce^{3+} , $\text{C}(\text{NH}_2)_3^+$, and $\text{OC}(\text{NH}_2)\text{NH}_3^+$ in aqueous solution leads to formations/assemblies which exhibit well-defined cation separations *at*, *above*, or *below* the capsules channel-landscapes (‘nano-ion chromatograph’ behaviour).¹⁴⁶ Taking this one step further a temperature-dependent equilibrium process that involves the uptake/release of Li^+ ions through the capsule pores has been observed: the porous capsule behaves as a semi-permeable inorganic membrane open for H_2O and small cations.¹⁴⁷ Furthermore, the 20 pores of the same capsule ‘shut’ by protonated urea as “stoppers”, can be opened in solution thus allowing calcium(II) ion uptake while later closing occurs again (see Fig. 22).¹⁴⁸ Remarkably, “pore gating”—just modelling biological ion transport—can illustratively be demonstrated: after initial cation uptake, subsequent cations are found hydrated above the pores due to a decrease of negative capsule charge.¹⁴⁹

5 Conclusions and perspectives in polyoxometalate chemistry: From biology to nanotechnology

In recent years there has been an unprecedented rise in the number of interesting POM clusters that have been structurally characterised by single crystal X-ray crystallography and, of course, the absolute size of the molecules characterised. Indeed, the elucidation of the structure of $\{\text{Mo}_{368}\}$ represents the largest non-biologically derived macromolecule to be

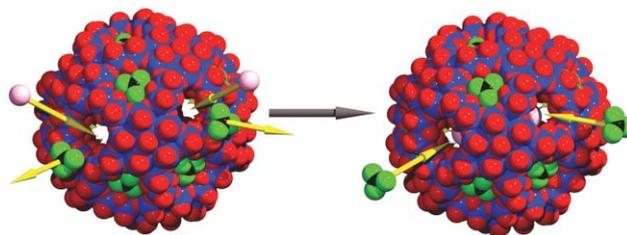


Fig. 22 Space-filling representation demonstrating a simplified view of the Ca^{2+} ion uptake based on the capsule $[\{(\text{Mo})(\text{Mo}_5\text{O}_{21}(\text{H}_2\text{O})_6)_{12}\{\text{Mo}_2\text{O}_4(\text{SO}_4)\}_{30}\}^{72-}]$. Initially the pores are closed, but treating a solution of the capsule with Ca^{2+} ions leads to cation uptake (left) while in the final product the pores again are closed (right; Mo-blue, O-red, C-black, N/O(urea)-green, Ca^{2+} -pink, yellow arrows indicate direction of motion).

structurally characterised to date and there is no reason to suppose that the discoveries in this area will stop at this nuclearity.

Polyoxometalates, with all their relevance to catalysis, reactivity, electronic structure, materials science and medicine are set to become a paradigm for those working in nanoscale science. This is because the POM clusters described here are ideal candidates for the development of a new type of supramolecular chemistry based upon the building-block ideas already established; using these ideas it should be possible to work towards designer nanomolecules of ever increasing size and complexity. Such clusters, for instance, are being proposed as models for biological ion transport pathways, as well as allowing the oxo-wall to be smashed in the isolation of a Pt=O species. They also are finding application as potential components for nanoscale computing devices. Maybe such systems could be used to probe and even discover new physics at the quantum classical limit or examine molecular growth processes. In addition, researchers could ask fundamental questions about the self assembly processes that underpin the creation of such structures and ask what influence could our concept of building geometrical and real building blocks have in the design of these molecules. If we are able to devise some rules for cluster design then it maybe possible to design new types of molecular hostage complexes that could be used in information storage or even in light harvesting systems, as well as potential application as robust sequestration agents. For example, there is potential to design POM clusters that can selectively assemble into a given structural type in the presence of the ion to be sequestered, *e.g.* actinide ions, to produce a system for sequestering radioactive elements. The design/discovery of POM nano-tubes and junctions would also be an important aspect and provide an interesting alternative to the carbon-based analogues. Whatever the future one thing is sure—that researchers will be captivated and motivated by the beauty and complexity of POM structures that will be discovered during the next years.

Acknowledgements

The authors would like to thank the EPSRC, Leverhulme Trust and the Royal Society for financial support.

References

- 1 A. Müller, E. Krickemeyer, J. Meyer, H. Bögge, F. Peters, W. Plass, E. Diemann, S. Dillinger, F. Nonnenbruch, M. Randerath and C. Menke, *Angew. Chem., Int. Ed. Engl.*, 1995, **34**, 2122.
- 2 A. Müller, E. Beckmann, H. Bögge, M. Schmidtman and A. Dress, *Angew. Chem., Int. Ed.*, 2002, **41**, 1162.
- 3 A. Müller and S. Roy, *Coord. Chem. Rev.*, 2003, **245**, 153.
- 4 T. B. Liu, E. Diemann, H. L. Li, A. W. M. Dress and A. Müller, *Nature*, 2003, **426**, 59.
- 5 C. L. Hill, *Chem. Rev.*, 1998, **98**, 1.
- 6 For example papers covering polyoxometalates in catalysis please see: N. M. Okun, T. Anderson and C. L. Hill, *J. Mol. Catal.*, 2003, **197**, 283–290; K. Kamata, K. Yonehara, Y. Sumida, K. Yamaguchi and N. Mizuno, *Science*, 2003, **300**, 964; A. M. Khenkin and R. Neumann, *J. Am. Chem. Soc.*, 2002, **124**, 4198; E. F. Kozhevnikova and I. V. Kozhevnikov, *J. Catal.*, 2004, **224**, 164.
- 7 M. T. Pope and A. Müller, *Angew. Chem., Int. Ed. Engl.*, 1991, **30**, 34.
- 8 M. I. Khan, *J. Solid State Chem.*, 2000, **152**, 105.
- 9 D. L. Long and L. Cronin, *Chem.–Eur. J.*, 2006, **12**, 3698.
- 10 H. Y. Ma, J. Peng, Z. G. Han, X. Yu and B. X. Dong, *J. Solid State Chem.*, 2005, **178**, 3735.
- 11 T. Yamase, *J. Mater. Chem.*, 2005, **15**, 4773.
- 12 B. Hasenknopf, *Front. Biosci.*, 2005, **10**, 275.
- 13 K. Nomiya, H. Torii, T. Hasegawa, Y. Nemoto, K. Nomura, K. Hashino, M. Uchida, Y. Kato, K. Shimizu and M. Oda, *Journal of Inorganic Biochemistry*, 2001, **86**, 657.
- 14 J. T. Rhule, C. L. Hill and D. A. Judd, *Chem. Rev.*, 1998, **98**, 327.
- 15 R. J. Errington, S. S. Petkar, B. R. Horrocks, A. Houlton, L. H. Lie and S. N. Patole, *Angew. Chem., Int. Ed.*, 2005, **44**, 1254.
- 16 M. V. Vasylyev and R. Neumann, *J. Am. Chem. Soc.*, 2004, **126**, 884.
- 17 R. Neumann, A. M. Khenkin and I. Vigdergauz, *Chem.–Eur. J.*, 2000, **6**, 875.
- 18 N. Mizuno, K. Yamaguchi and K. Kamata, *Coord. Chem. Rev.*, 2005, **249**, 1944.
- 19 I. M. Mbomekalle, B. Keita, L. Nadjo, P. Berthet, K. I. Hardcastle, C. L. Hill and T. M. Anderson, *Inorg. Chem.*, 2003, **42**, 1163.
- 20 D. Volkmer, B. Bredenkotter, J. Tellenbroker, P. Kögerler, D. G. Kurth, P. Lehmann, H. Schnablegger, D. Schwahn, M. Piepenbrink and B. Krebs, *J. Am. Chem. Soc.*, 2002, **124**, 10489.
- 21 S. Q. Liu, D. Volkmer and D. G. Kurth, *J. Cluster Sci.*, 2003, **14**, 405.
- 22 G. Chaidogiannos, D. Velessiotis, P. Argitis, P. Koutsoloulos, C. D. Diakoumakos, D. Tsamakias and N. Glezos, *Microelectron. Eng.*, 2004, **73–74**, 746.
- 23 S. Q. Liu, H. Mohwald, D. Volkmer and D. G. Kurth, *Langmuir*, 2006, **22**, 1949.
- 24 S. Q. Liu, D. G. Kurth, H. Mohwald and D. Volkmer, *Adv. Mater.*, 2002, **14**, 225.
- 25 S. Q. Liu, D. Volkmer and D. G. Kurth, *Anal. Chem.*, 2004, **76**, 4579.
- 26 S. Q. Liu, D. G. Kurth and D. Volkmer, *Chem. Commun.*, 2002, 976.
- 27 E. Coronado, C. Gimenez-Saiz and C. J. Gomez-Garcia, *Coord. Chem. Rev.*, 2005, **249**, 1776.
- 28 E. Coronado, S. Curreli, C. Gimenez-Saiz, C. J. Gomez-Garcia and J. Roth, *Synth. Met.*, 2005, **154**, 241.
- 29 L. Xu, E. B. Wang, Z. Li, D. G. Kurth, X. G. Du, H. Y. Zhang and C. Qin, *New J. Chem.*, 2002, **26**, 782.
- 30 M. Luban, F. Borsa, S. Bud'ko, P. C. Canfield, S. Jun, J. K. Jung, P. Kögerler, D. Mentrup, A. Müller, R. Modler, D. Prociassi, B. J. Suh and M. Torikachvili, *Phys. Rev. B: Condens. Matter*, 2002, **66**.
- 31 M. T. Pope, Isopolyanions and Heteropolyanions, *Comprehensive Coordination Chemistry*, ed. G. Wilkinson, R. D. Gillard, and J. A. McCleverty, Pergamon Press, Oxford, 1987, vol. 3, p. pp. 1023–1058.
- 32 K. Wassermann, M. H. Dickman and M. T. Pope, *Angew. Chem., Int. Ed. Engl.*, 1997, **36**, 1445.
- 33 L. Cronin, in *High Nuclearity Clusters*, ed. J. A. McCleverty and T. J. Meyer, Elsevier, Amsterdam, 2004.
- 34 W. Scheele, in *Sämtliche Physische und Chemische Werke*, ed. D. S. F. Hermbstädt, M. Sändig oHG, Niederwalluf/Wiesbaden, 1971.
- 35 A. Müller, E. Krickemeyer, H. Bögge, M. Schmidtman and F. Peters, *Angew. Chem., Int. Ed.*, 1998, **37**, 3360.
- 36 L. Cronin, C. Beugholt, E. Krickemeyer, M. Schmidtman, H. Bögge, P. Kögerler, T. K. K. Luong and A. Müller, *Angew. Chem., Int. Ed.*, 2002, **41**, 2805.
- 37 M. T. Pope, *Heteropoly and Isopoly Oxometalates*, Springer-Verlag, Berlin, 1983.
- 38 J. Zubieta, in *Comprehensive Coordination Chemistry II*, ed. J. A. McCleverty and T. J. Meyer, Elsevier, Amsterdam, 2004, vol. 1, p. 697.
- 39 C. D. Wu, C. Z. Lu, H. H. Zhuang and J. S. Huang, *J. Am. Chem. Soc.*, 2002, **124**, 3836.
- 40 X. M. Zhang, H. S. Wu, F. Q. Zhang, A. Prikhod'ko, S. Kuwata and P. Comba, *Chem. Commun.*, 2004, 2046.

- 41 N. Belai, M. Sadakane and M. T. Pope, *J. Am. Chem. Soc.*, 2001, **123**, 2087.
- 42 I. Bruedgam, J. Fuchs, H. Hartl and R. Palm, *Angew. Chem., Int. Ed.*, 1998, **37**, 2668.
- 43 D. W. Lewis, D. J. Willock, C. R. A. Catlow, J. M. Thomas and G. J. Hutchings, *Nature*, 1996, **382**, 604.
- 44 D. L. Long, P. Kögerler, L. J. Farrugia and L. Cronin, *Angew. Chem., Int. Ed.*, 2003, **42**, 4180.
- 45 D. L. Long, P. Kögerler, L. J. Farrugia and L. Cronin, *Dalton Trans.*, 2005, 1372.
- 46 D. L. Long, H. Abbas, P. Kögerler and L. Cronin, *J. Am. Chem. Soc.*, 2004, **126**, 13880.
- 47 D. L. Long, O. Brücher, C. Streb and L. Cronin, *Dalton Trans.*, 2006, 2852.
- 48 D. L. Long, P. Kögerler, A. D. C. Parenty, J. Fielden and L. Cronin, *Angew. Chem., Int. Ed.*, 2006, **45**, 4798.
- 49 Y. Jeannin, *C. R. Acad. Sci., Ser. IIc: Chim.*, 2001, **4**, 683.
- 50 B. Krebs, E. Droste, M. Piepenbrink and G. Vollmer, *C. R. Acad. Sci., Serie IIc: Chim.*, 2000, **3**, 205.
- 51 D. L. Long, P. Kögerler and L. Cronin, *Angew. Chem., Int. Ed.*, 2004, **43**, 1817.
- 52 D. L. Long, H. Abbas, P. Kögerler and L. Cronin, *Angew. Chem., Int. Ed.*, 2005, **44**, 3415.
- 53 U. Körtz and M. T. Pope, *Inorg. Chem.*, 1994, **33**, 5643.
- 54 U. Körtz, *Inorg. Chem.*, 2000, **39**, 623.
- 55 I. M. Mbomekalle, B. Keita, Y. W. Lu, L. Nadjjo, R. Contant, N. Belai and M. T. Pope, *Eur. J. Inorg. Chem.*, 2004, 4132.
- 56 N. Belai, M. H. Dickman, M. T. Pope, R. Contant, B. Keita, I. M. Mbomekalle and L. Nadjjo, *Inorg. Chem.*, 2005, **44**, 169.
- 57 K. C. Kim and M. T. Pope, *J. Am. Chem. Soc.*, 1999, **121**, 8512.
- 58 K. C. Kim and M. T. Pope, *J. Chem. Soc., Dalton Trans.*, 2001, 986.
- 59 A. J. Gaunt, I. May, R. Copping, A. I. Bhatt, D. Collison, O. D. Fox, K. T. Holman and M. T. Pope, *Dalton Trans.*, 2003, 3009.
- 60 K. Wassermann and M. T. Pope, *Inorg. Chem.*, 2001, **40**, 2763.
- 61 P. Mialane, A. Dolbecq, E. Riviere, J. Marrot and F. Secheresse, *Eur. J. Inorg. Chem.*, 2004, 33.
- 62 P. Mialane, L. Lisnard, A. Mallard, J. Marrot, E. Antic-Fidancev, P. Aschehoug, D. Vivien and F. Secheresse, *Inorg. Chem.*, 2003, **42**, 2102.
- 63 D. Quinonero, Y. Wang, K. Morokuma, L. A. Khavrutskii, B. Botar, Y. V. Geletii, C. L. Hill and D. G. Musaev, *J. Phys. Chem. B*, 2006, **110**, 170.
- 64 L. H. Bi, M. H. Dickman, U. Körtz and I. Dix, *Chem. Commun.*, 2005, 3962.
- 65 L. H. Bi, U. Körtz, B. Keita, L. Nadjjo and H. Borrmann, *Inorg. Chem.*, 2004, **43**, 8367.
- 66 L. H. Bi, U. Körtz, B. Keita, L. Nadjjo and L. Daniels, *Eur. J. Inorg. Chem.*, 2005, 3034.
- 67 U. Körtz, M. G. Savelieff, B. S. Bassil and M. H. Dickman, *Angew. Chem., Int. Ed.*, 2001, **40**, 3384.
- 68 T. M. Anderson, W. A. Neiwert, M. L. Kirk, P. M. B. Piccoli, A. J. Schultz, T. F. Koetzle, D. G. Musaev, K. Morokuma, R. Cao and C. L. Hill, *Science*, 2004, **306**, 2074.
- 69 T. M. Anderson, R. Cao, E. Slonkina, B. Hedman, K. O. Hodgson, K. I. Hardcastle, W. A. Neiwert, S. X. Wu, M. L. Kirk, S. Knottenbelt, E. C. Depperman, B. Keita, L. Nadjjo, D. G. Musaev, K. Morokuma and C. L. Hill, *J. Am. Chem. Soc.*, 2005, **127**, 11948.
- 70 B. Godin, J. Vaissermann, P. Herson, L. Ruhlmann, M. Verdager and P. Gouzerh, *Chem. Commun.*, 2005, 5624.
- 71 S. S. Mal and U. Körtz, *Angew. Chem., Int. Ed.*, 2005, **44**, 3777.
- 72 B. S. Bassil, S. Nellutla, U. Körtz, A. C. Stowe, J. van Tol, N. S. Dalal, B. Keita and L. Nadjjo, *Inorg. Chem.*, 2005, **44**, 2659.
- 73 W. B. Yang, C. H. Lu, Q. Z. Zhang, S. M. Chen, X. P. Zhan and J. H. Liu, *Inorg. Chem.*, 2003, **42**, 7309.
- 74 M. I. Khan, S. Ayesh, R. J. Doedens, M. H. Yu and C. J. O'Connor, *Chem. Commun.*, 2005, 4658.
- 75 L. Chen, F. L. Jiang, Z. Z. Lin, Y. F. Zhou, C. Y. Yue and M. C. Hong, *J. Am. Chem. Soc.*, 2005, **127**, 8588.
- 76 M. Nyman, F. Bonhomme, T. M. Alam, M. A. Rodriguez, B. R. Cherry, J. L. Krumhansl, T. M. Nenoff and A. M. Sattler, *Science*, 2002, **297**, 996.
- 77 M. Nyman, F. Bonhomme, T. M. Alam, J. B. Parise and G. M. B. Vaughan, *Angew. Chem., Int. Ed.*, 2004, **43**, 2787.
- 78 M. Nyman, A. J. Celestian, J. B. Parise, G. P. Holland and T. M. Alam, *Inorg. Chem.*, 2006, **45**, 1043.
- 79 A. Müller and C. Serain, *Acc. Chem. Res.*, 2000, **33**, 2.
- 80 A. Müller, P. Kögerler and A. W. M. Dress, *Coord. Chem. Rev.*, 2001, **222**, 193.
- 81 A. Müller and P. Kögerler, *Coord. Chem. Rev.*, 2000, **199**, 335.
- 82 L. Cronin, C. Beugholt and A. Müller, *THEOCHEM*, 2000, **500**, 181.
- 83 A. Müller, S. Sarkar, S. Q. N. Shah, H. Bögge, M. Schmidtman, S. Sarkar, P. Kögerler, B. Hauptfleisch, A. X. Trautwein and V. Schunemann, *Angew. Chem., Int. Ed.*, 1999, **38**, 3238.
- 84 F. Secheresse, A. Dolbecq, P. Mialane and E. Cadot, *C. R. Chim.*, 2005, **8**, 1927.
- 85 V. Bereau, E. Cadot, H. Bögge, A. Müller and F. Secheresse, *Inorg. Chem.*, 1999, **38**, 5803.
- 86 E. Cadot, B. Salignac, S. Halut and F. Secheresse, *Angew. Chem., Int. Ed.*, 1998, **37**, 611.
- 87 E. Cadot, B. Salignac, T. Loiseau, A. Dolbecq and F. Secheresse, *Chem.–Eur. J.*, 1999, **5**, 3390.
- 88 E. Cadot, M. J. Pouet, C. R. Robert-Labarre, C. du Peloux, J. Marrot and F. Secheresse, *J. Am. Chem. Soc.*, 2004, **126**, 9127.
- 89 A. Dolbecq, E. Cadot and F. Secheresse, *Chem. Commun.*, 1998, 2293.
- 90 E. Cadot, A. Dolbecq, B. Salignac and F. Secheresse, *Chem.–Eur. J.*, 1999, **5**, 2396.
- 91 A. Dolbecq, E. Cadot and F. Secheresse, *C. R. Acad. Sci., Serie IIc: Chim.*, 2000, **3**, 193.
- 92 B. Salignac, S. Riedel, A. Dolbecq, F. Secheresse and E. Cadot, *J. Am. Chem. Soc.*, 2000, **122**, 10381.
- 93 A. Dolbecq, C. du Peloux, A. L. Auberty, S. A. Mason, P. Barboux, J. Marrot, E. Cadot and F. Secheresse, *Chem.–Eur. J.*, 2002, **8**, 350.
- 94 E. Cadot, M. A. Pilette, M. Marrot and F. Secheresse, *Angew. Chem., Int. Ed.*, 2003, **42**, 2173.
- 95 M. J. Manos, J. D. Woollins, A. M. Z. Slawin and T. A. Kabanos, *Angew. Chem., Int. Ed.*, 2002, **41**, 2801.
- 96 H. N. Miras, J. D. Woollins, A. M. Slawin, R. Raptis, P. Baran and T. A. Kabanos, *Dalton Trans.*, 2003, 3668.
- 97 M. J. Manos, H. N. Miras, V. Tangoulis, J. D. Woollins, A. M. Z. Slawin and T. A. Kabanos, *Angew. Chem., Int. Ed.*, 2003, **42**, 425.
- 98 C. Bustos, B. Hasenknopf, R. Thouvenot, J. Vaissermann, A. Proust and P. Gouzerh, *Eur. J. Inorg. Chem.*, 2003, 2757.
- 99 C. Dablemont, A. Proust, R. Thouvenot, C. Afonso, F. Fournier and J. C. Tabet, *Inorg. Chem.*, 2004, **43**, 3514.
- 100 S. Bareyt, S. Piligkos, B. Hasenknopf, P. Gouzerh, E. Lacote, S. Thorimbert and M. Malacria, *Angew. Chem., Int. Ed.*, 2003, **42**, 3404.
- 101 R. Villanneau, R. Delmont, A. Proust and P. Gouzerh, *Chem.–Eur. J.*, 2000, **6**, 1184.
- 102 D. Laurencin, R. Villanneau, P. Herson, R. Thouvenot, Y. Jeannin and A. Proust, *Chem. Commun.*, 2005, 5524.
- 103 V. Artero, A. Proust, P. Herson, F. Villain, C. C. D. Moulin and P. Gouzerh, *J. Am. Chem. Soc.*, 2003, **125**, 11156.
- 104 U. Körtz, F. Hussain and M. Reicke, *Angew. Chem., Int. Ed.*, 2005, **44**, 3773.
- 105 S. Favette, B. Hasenknopf, J. Vaissermann, P. Gouzerh and C. Roux, *Chem. Commun.*, 2003, 2664.
- 106 B. Hasenknopf, R. Delmont, P. Herson and P. Gouzerh, *Eur. J. Inorg. Chem.*, 2002, 1081.
- 107 A. Müller and S. Roy, *Eur. J. Inorg. Chem.*, 2005, 3561.
- 108 A. Müller, S. K. Das, M. O. Talismanova, H. Bögge, P. Kögerler, M. Schmidtman, S. S. Talismanov, M. Luban and E. Krickemeyer, *Angew. Chem., Int. Ed.*, 2002, **41**, 579.
- 109 B. B. Xu, Z. H. Peng, Y. G. Wei and D. R. Powell, *Chem. Commun.*, 2003, 2562.
- 110 Z. H. Peng, *Angew. Chem., Int. Ed.*, 2004, **43**, 930.
- 111 J. Kang, B. B. Xu, Z. H. Peng, X. D. Zhu, Y. G. Wei and D. R. Powell, *Angew. Chem., Int. Ed.*, 2005, **44**, 6902.
- 112 W. Ouellette, V. Golub, C. J. O'Connor and J. Zubieta, *Dalton Trans.*, 2005, 291.
- 113 E. Burkholder, V. Golub, C. J. O'Connor and J. Zubieta, *Inorg. Chem.*, 2004, **43**, 7014.

- 114 C. Cannizzo, C. R. Mayer, F. Secheresse and C. Larpent, *Adv. Mater.*, 2005, **17**, 2888.
- 115 H. Abbas, A. L. Pickering, D. L. Long, P. Kögerler and L. Cronin, *Chem.–Eur. J.*, 2005, **11**, 1071.
- 116 D. Sloboda-Rozner, P. Witte, P. L. Alsters and R. Neumann, *Adv. Synth. Catal.*, 2004, **346**, 339.
- 117 A. Müller, M. Luban, C. Schröder, R. Modler, P. Kögerler, M. Axenovich, J. Schnack, P. C. Canfield, S. Bud'ko and N. Harrison, *ChemPhysChem*, 2001, **2**, 517.
- 118 B. Botar, P. Kögerler, A. Müller, R. Garcia-Serres and C. L. Hill, *Chem. Commun.*, 2005, 5621.
- 119 A. Müller, A. M. Todea, J. van Slageren, M. Dressel, H. Bögge, M. Schmidtman, M. Luban, L. Engelhardt and M. Rusu, *Angew. Chem., Int. Ed.*, 2005, **44**, 3857.
- 120 P. Mialane, A. Dolbecq, J. Marrot, E. Riviere and F. Secheresse, *Chem.–Eur. J.*, 2005, **11**, 1771.
- 121 P. Mialane, A. Dolbecq, J. Marrot, E. Riviere and F. Secheresse, *Angew. Chem., Int. Ed.*, 2003, **42**, 3523.
- 122 E. Coronado, J. R. Galan-Mascaros, C. Gimenez-Saiz, C. J. Gomez-Garcia, E. Martinez-Ferrero, M. Almeida and E. B. Lopes, *Adv. Mater.*, 2004, **16**, 324.
- 123 A. Lapinski, V. Starodub, M. Golub, A. Kravchenko, V. Baumer, E. Faulques and A. Graja, *Synth. Met.*, 2003, **138**, 483.
- 124 E. Coronado, C. Gimenez-Saiz, C. J. Gomez-Garcia and S. C. Capelli, *Angew. Chem., Int. Ed.*, 2004, **43**, 3022.
- 125 H. Y. An, E. B. Wang, D. R. Xiao, Y. G. Li, Z. M. Su and L. Xu, *Angew. Chem., Int. Ed.*, 2006, **45**, 904.
- 126 M. Lu, J. H. Kang, D. G. Wang and Z. H. Peng, *Inorg. Chem.*, 2005, **44**, 7711.
- 127 W. Adam, P. L. Alsters, R. Neumann, C. R. Saha-Moller, D. Seebach, A. K. Beck and R. Zhang, *J. Org. Chem.*, 2003, **68**, 8222.
- 128 G. Maayan, R. H. Fish and R. Neumann, *Org. Lett.*, 2003, **5**, 3547.
- 129 C. D. Wu, C. Z. Lu, X. Lin, D. M. Wu, S. F. Lu, H. H. Zhuang and J. S. Huang, *Chem. Commun.*, 2003, 1284.
- 130 M. Sadakane, M. H. Dickman and M. T. Pope, *Inorg. Chem.*, 2001, **40**, 2715.
- 131 P. P. Fu, X. L. Wang, E. B. Wang, C. Qin and L. Xu, *Chem. Res. Chin. Univ.*, 2005, **21**, 509.
- 132 S. J. Xue, S. Y. Ke, L. Yan, Z. J. Cai and Y. G. Wei, *J. Inorg. Biochem.*, 2005, **99**, 2276.
- 133 D. C. Crans, J. J. Smee, E. Gaidamauskas and L. Q. Yang, *Chem. Rev.*, 2004, **104**, 849.
- 134 Y. Zhang, X. D. Yang, K. Wang and D. C. Crans, *J. Inorg. Biochem.*, 2006, **100**, 80.
- 135 P. Buglyo, D. C. Crans, E. M. Nagy, R. L. Lindo, L. Q. Yang, J. J. Smee, W. Z. Jin, L. H. Chi, M. E. Godzala and G. R. Willsky, *Inorg. Chem.*, 2005, **44**, 5416.
- 136 G. Liu and T. B. Liu, *Langmuir*, 2005, **21**, 2713.
- 137 S. Polarz, B. Smarsly and M. Antonietti, *ChemPhysChem*, 2001, **2**, 457.
- 138 D. G. Kurth, P. Lehmann, D. Volkmer, H. Colfen, M. J. Koop, A. Müller and A. Du Chesne, *Chem.–Eur. J.*, 2000, **6**, 385.
- 139 D. Volkmer, A. Du Chesne, D. G. Kurth, H. Schnablegger, P. Lehmann, M. J. Koop and A. Müller, *J. Am. Chem. Soc.*, 2000, **122**, 1995.
- 140 D. G. Kurth, P. Lehmann, D. Volkmer, A. Müller and D. Schwahn, *J. Chem. Soc., Dalton Trans.*, 2000, 3989.
- 141 D. G. Kurth, D. Volkmer, M. Ruttorf, B. Richter and A. Müller, *Chem. Mater.*, 2000, **12**, 2829.
- 142 S. Q. Liu, D. G. Kurth, B. Bredenkotter and D. Volkmer, *J. Am. Chem. Soc.*, 2002, **124**, 12279.
- 143 A. Müller, E. Krickemeyer, H. Bögge, M. Schmidtman, B. Botar and M. O. Talismanova, *Angew. Chem., Int. Ed.*, 2003, **42**, 2085.
- 144 A. Müller, E. Krickemeyer, H. Bögge, M. Schmidtman, S. Roy and A. Berkle, *Angew. Chem., Int. Ed.*, 2002, **41**, 3604.
- 145 A. Müller, B. Botar, H. Bögge, P. Kögerler and A. Berkle, *Chem. Commun.*, 2002, 2944.
- 146 A. Müller, S. K. Das, S. Talismanov, S. Roy, E. Beckmann, H. Bögge, M. Schmidtman, A. Merca, A. Berkle, L. Allouche, Y. S. Zhou and L. J. Zhang, *Angew. Chem., Int. Ed.*, 2003, **42**, 5039.
- 147 A. Müller, D. Rehder, E. T. K. Haupt, A. Merca, H. Bögge, M. Schmidtman and G. Heinze-Bruckner, *Angew. Chem., Int. Ed.*, 2004, **43**, 4466.
- 148 A. Müller, L. Toma, H. Bögge, C. Schaffer and A. Stammler, *Angew. Chem., Int. Ed.*, 2005, **44**, 7757.
- 149 A. Müller, Y. Zhou, H. Bögge, M. Schmidtman, T. Mitra, E. T. K. Haupt and A. Berkle, *Angew. Chem., Int. Ed.*, 2006, **45**, 460.